

Paper 18 open access : Comprehensive Characterization Of Novel Cellulose Fiber From Paederia Foetida and Its Modification For Sustainable Composites Application

Full paper dapat dilihat di bagian bawah ini



Comprehensive Characterization Of Novel Cellulose Fiber From Paederia Foetida and Its Modification For Sustainable Composites Application

2023 - Volume 26 **Volume 26, Issue 10** 09 February 2023 Reach: 600



Environmental Engineering

Nasmi Herlina Sari¹, Edi Syafri²,
Suteja¹, Widya Fatriasari³, and
Azizatul Karimah³



Editor-in-Chief



Chi-Wang Li, Tamkang University, Taiwan

Chi-Wang Li

Chi-Wang Li is a Professor of the Department of Water Resource and Environmental Engineering, TamKang University, Taipei, Taiwan. His main areas of research interest are the integration of membrane with different physical and chemical processes for water and wastewater treatment.

Co-Editor-in-Chief



Kyungpook National University, South Korea

Kwang-Ho Choo

Kwang-Ho Choo is a Professor in the Department of Environmental Engineering and the Director of the Advanced Institute of Water Industry at Kyungpook National University. Dr. Choo's research has focused on the hybridization of membrane technology treatment for water quality enhancement and membrane fouling control.



Prabhat Hajela

Rensselaer Polytechnic Institute,
USA.



Qing Li

City University of Hong Kong,
Hong Kong



Sheng-Hsien Lin

National Chao Tung University,
Taiwan



Son T. Vuong

University of British Columbia,
Canada



Timothy Arndt

Cleveland State University, USA.



Xiaofang Zhou

University of Queensland,
Australia



Yanchun Zhang

Victoria University, Australia



Yoshitaka Shibata

Iwate Prefectural University,
Japan

Journal of Applied Science and Engineering (Taiwan)

COUNTRY Taiwan Universities and research institutions in Taiwan Media Ranking in Taiwan	SUBJECT AREA AND CATEGORY Engineering ↳ Engineering (miscellaneous) Multidisciplinary ↳ Multidisciplinary	PUBLISHER Tamkang University Tamkang University in Scimago Institutions Rankings	H-INDEX <h1>29</h1>
PUBLICATION TYPE Journals	ISSN 27089967, 27089975	COVERAGE 2021-2022	INFORMATION Homepage How to publish in this journal

Journal of Applied Science and Engineering (Taiwan)

Q3 Engineering (miscellaneous) best quartile

SJR 2021 0.22

powered by scimagojr.com

Show this widget in your own website

Just copy the code below and paste within your html code:

``

SCImago Graphica

Explore, visually communicate and make sense of data with our new data visualization tool.

S&P Global Market Intelligence

Don't just make sustainability progress. Measure it.

Seek & Prosper Align your impact >

Source details

Journal of Applied Science and Engineering (Taiwan)
 Formerly known as: *Journal of Applied Science and Engineering*
 Scopus coverage years: from 2021 to Present
 Publisher: Tamkang University
 ISSN: 2708-9967 E-ISSN: 2708-9975
 Subject area: (Multidisciplinary) (Engineering: General Engineering)
 Source type: Journal

CiteScore 2021: 0.9
 SJR 2021: 0.218
 SNIP 2021: 0.340

Improved CiteScore methodology
 CiteScore 2021 counts the citations received in 2018-2021 to articles, reviews, conference papers, book chapters and data papers published in 2018-2021, and divides this by the number of publications published in 2018-2021. [Learn more](#)

CiteScore 2021 | CiteScoreTracker 2022

Volume 26, Issue 10

Comprehensive Characterization Of Novel Cellulose Fiber From Paederia Foetida and Its Modification For Sustainable Composites Application

2023 - Volume 26 **Volume 26, Issue 10** 09 February 2023
 Reach: 600



Integrated Computational Materials Engineering With Reliability Of Green Concrete (GC) For Environmental Safety Buildings

2023 - Volume 26 **Volume 26, Issue 10** 09 February 2023
 Reach: 229



Novel Categories Of Analytical Solutions To The Calogero-Bogoyavlenskii-Schiff Equation

Emergent Pressure Dynamics In Coupled Nephron Compliance Tubular Model Using Cellular Automata Rules

2023 - Volume 26 **Volume 26, Issue 10** 22 December 2022

Reach: 704

1

Steer Guidance Of Autonomous Agricultural Robot Based On Pure Pursuit Algorithm And LiDAR Based Vector Field Histogram

2023 - Volume 26 **Volume 26, Issue 10** 04 January 2023 Reach: 466

1

Comprehensive Characterization Of Novel Cellulose Fiber From *Paederia Foetida* and Its Modification For Sustainable Composites Application

Nasmi Herlina Sari^{1*}, Edi Syafri², Suteja¹, Widya Fatriasari³, and Azizatul Karimah³

¹ Department of Mechanical Engineering, Faculty of Engineering, University of Mataram, Mataram, West Nusa Tenggara 83125, Indonesia

² Department of Agricultural Technology, Politeknik Pertanian Negeri Payakumbuh, Payakumbuh, West Sumatera 26271, Indonesia

³ Research Center for Biomass and Bioproducts, National Research and Innovation Agency (BRIN), Jl. Raya Bogor Km 46, Cibinong, Bogor 16911, Indonesia

* Corresponding author. E-mail: n.herlinasari@unram.ac.id

Received: Sep. 20, 2022; Accepted: Nov. 28, 2022

Fiber derived from the plant *Paederia Foetida* stems (PF) is a novel natural fiber with the capacity to replace glass fibers in composite reinforcement. The technique of modifying the fiber surface with NaOH and KOH is simple and straightforward, generating properties that differ from the raw fiber. Therefore, this study aims to investigate the effects of NaOH and KOH treatments on the surface of *Paederia foetida* fiber (PFs) in relation to the physical, crystal structure, functional groups, tensile strength, thermal and morphological properties compared to raw PFs. The raw fiber was obtained by soaking the PFs rods in water for 10 days, followed by surface treatment with a solution of NaOH and KOH. The results showed that compared to raw fiber, after NaOH dan KOH treated PFs, the diameter and moisture content of the PFs decreased, while the tensile strength increased significantly by 43.27%, and good thermal stability. The highest crystallinity index was obtained from KOH-treated PFs of 79.685%. According to the functional groups in the FTIR observations, NaOH treatment was found to be more effective in removing lignin and hemicellulose components, as well as increasing cellulose compounds in the fiber. The surface morphology was found to be rougher with the loss of impurities after NaOH treatment. Based on the results, raw, NaOH and KOH-treated PFs have the potential to be used as reinforcement for lightweight composite and alternative materials to replace glass fiber and coconut fiber in construction applications.

Keywords: Chemical; KOH; mechanical properties; NaOH; *Paederia foetida* fiber (PFs); physical properties

© The Author(s). This is an open-access article distributed under the terms of the [Creative Commons Attribution License \(CC BY 4.0\)](https://creativecommons.org/licenses/by/4.0/), which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are cited.

[http://dx.doi.org/10.6180/jase.202310_26\(10\).0005](http://dx.doi.org/10.6180/jase.202310_26(10).0005)

1. Introduction

Nature has provided various renewable and environmentally friendly resources that have many potentials uses for textile fibers and composite materials. Natural fibers can be produced from any part of the plant and used in a wide range of applications, including fibers and textiles for composite applications [1–5]. In recent decades, new natural fibers with their best properties have been investigated and characterized such as corn husk fiber [1], *Juncus* plant [2],

Hibiscus tiliceaus fiber [6], *Sterculia foetida* fruit shell fiber [5, 7], *Musaceae* and *Saccharum officinarum* Cellulose Fibers [8], etc. Furthermore, the lignocellulosic natural fiber is known to have strength and stiffness properties comparable to glass fiber, as well as low density, and non-abrasive [1, 9, 10]. These unique traits and properties have created opportunities for the investigation and development of various natural fibers.

One source of natural fiber that has not been utilized optimally is *Paederia foetida* (PF) which grows convoluted

vines, as well as forms shrubs and annuals. Furthermore, PF leaves belong to the *Rubiceae* tribe, have soft stems, and are used for climbing trees. They are only half a centimeter in diameter but can reach 10 m in length. Several investigations have been conducted on the PF plant in relation to the use of drugs in the health sector, such as anti-rheumatic, analgesics, mucolytics, appetite enhancers, antibiotics, anti-inflammatory, cough medicines or anti-tussive, and diarrhea medication [11]. However, there is no information related to the use of fiber from the PF plant as a filler for composite materials. The abundant and eco-friendly fiber sources from this plant need to be developed to achieve excellent mechanical, physical, and thermal durability, as well as for wider applications.

Several investigations on the reinforcing of natural fibers in polymer composite materials to obtain desired qualities have been conducted. However, the developed composites often experience mechanical failures such as fiber pullout and debonding with the matrix. This failure is presumably due to the poor adhesion between hydrophobic (polymer) and hydrophilic (fibers), culminating in poor mechanical properties [12, 13]. Fortunately, Natural fibers' hydrophilic qualities can be lowered chemically by treating them with NaOH, silane, KOH, and peroxide [6, 8, 14]. Sari et al. [3] reported that the tensile strength of a single cornhusk fiber was enhanced to 368.25 MPa after being modified with NaOH from 0.5 to 8% for 2 hours. Furthermore, Shanmugasundaram & Ramkumar [15] stated that the cellulose content of betel leaf fiber of 57.49% can be increased to 68.54% after treatment with 5% NaOH. Sari and Padang, [6] also reported that the tensile strength of *T. hibiscus* fiber after treatment with 8% KOH reached 5144.9 MPa, while the surface of the fiber became cleaner, rougher, and fibrillar. Khan et al. [16] mentioned that banana fiber improved the mechanical properties after the treatment with NaOH solution. It was also discovered that the epoxy composite with banana fiber reinforcement treated with 4.5% NaOH had the greatest improvement in both compressive and tensile strength, with 24.2% and 34% increases, respectively. The optimal epoxy composite strength was obtained at 25.4 MPa or increased by 38% after banana fiber was treated with 6.5% NaOH. Mat Nasir et al. [17] also reported that after being treated with 6-10 wt% sodium hydroxide (NaOH) solution for 24 hours, Lemba Leaves Fibers (LeLeF) have fiber diameters in the range of 191.37 μm - 36.81 μm , and tensile properties in the range of 14.45 - 511.10 MPa, where the resulting properties are better than raw fiber. The mechanical properties and thermal stability of the fiber after NaOH treatment are superior to raw catfish fiber. Maity et al. [18] investigated the characteristics and uses of jute

and nonwoven-based composites. Meanwhile, Liu et al. [19] gathered *Sterculia* and *Foetida* plant stalk debris and slices it long and short, with an average length of around 38 mm and 16 mm, to make environmentally sustainable light translucent concrete. Furthermore, alkaline treatment has been shown to increase the moisture retention of biomass while decreasing the activation energy of rice husks. While it is known that sample pre-treatment increases the drying rate and effective diffusivity of rice husks [20]. This previous study shows that the properties of new natural fibers need to be investigated and developed. The unique properties of different, abundant, and environmentally friendly natural fibers need to be considered to encounter composite reinforcing materials. The modification of natural fibers also needs to be investigated to ensure the best properties which can provide added value to natural fibers.

Therefore, the purpose of this study was to provide detailed information on the extraction and evaluation of new natural fibers from the fiber stems of the plant *Paederia foetida* (PFs). The characteristics of the fiber were investigated through changes in morphology, tensile strength, thermal resistance, crystallinity index, and functional groups. The properties of the raw materials used will be compared to those of the fiber post-treatment with NaOH and KOH.

2. Experimental program

2.1. Materials

Paederia foetida plant in Fig. 1a was collected from Batukliang, Lombok, Indonesia, the stems were separated from the leaves manually, then sliced to lengths of 150 mm (Fig. 1b). Furthermore, a solution of 5% sodium hydroxide (5% NaOH) and 5% potassium hydroxide (5% KOH) was used as alkali treatment. It was obtained from the Biochemistry Laboratory, Faculty of Food Technology and Agricultural Products, University of Mataram.

2.2. Extraction of *Paederia foetida* fiber

The PF were soaked for 10 days in fresh water (Fig. 1c) to allow them to rot, then, the fibers from the rods were removed using a plastic comb to maintain a uniform diameter, subsequently, they were air-dried and prepared to be tested (Fig. 1d).

2.3. Alkali treatment of PFs

The PFs were immersed in 5% NaOH and 5% KOH alkaline solutions for 2 h at room temperature of 28 oC. Next, they were washed with distilled water four times to remove the remaining alkaline solution, followed by drying in the sun.



Fig. 1. *Paederia foetida*, PF, (a) plant, (b) selection of PF stems, (c) Soaking PF in water, (d) Extracting fiber from PF stems.

Below is the reaction scheme [1, 8].



Following that, the PFs were placed in a dry plastic container with a humidity of 20%; Fig. 2 depicts the alkaline treatment method for PFs. Raw fibers as well as those treated with NaOH, and KOH are shown in Fig. 3.

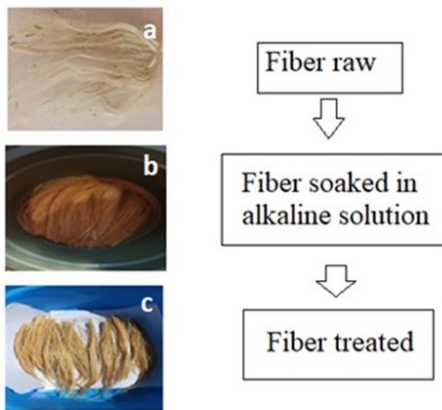


Fig. 2. Alkaline treatment process of PFs (a) fiber raw, (b) alkalization, and (c) dry PFs.

2.4. Characterization

2.4.1. Fiber density and diameter

A single PF sample was cut into small splices and placed on a microscope slide, then the raw and alkali-treated fiber diameters were measured using optical microscopy. A randomly selected 10 samples were measured at five locations along the length, and the average diameter value was reported.



Fig. 3. PFs (a) raw, (b) KOH treated dan (c) NaOH treated.

Furthermore, the buoyancy force was calculated by weighing PFs first in air and then in distilled water. The weighing was done using an analytical balance with a resolution of 0.001 g and was adapted for suspension weighing using a stainless-steel wire with a diameter of approximately 0.4 mm. By dividing the liquid density by the buoyancy force, sample volume was calculated. The density ρ_f was calculated by dividing the sample weight in air by the volume of the sample [1, 14].

$$\rho_f = \frac{(m_3 - m_1)}{(m_3 - m_1) - (m_4 - m_2)} \rho_w \quad (3)$$

where ρ_f is the fiber density (g/cm^3), and m_1 and m_2 are the weights of suspension wire in air and liquid, respectively. m_3 and m_4 represent the weight of the wire plus the sample weight in air and liquid (g), respectively. $\rho_w = 0.998 \text{ g}/\text{cm}^3$ (standard density of distilled water). All densities were measured using a Mettler Toledo measurement kit at $23 \pm 0.2^\circ\text{C}$ [14].

2.4.2. Moisture content

Water absorption has an impact on the physical properties of composites as well as the PFs-matrix interface [21]. The lowered hydrophilic hydroxyl groups increased the moisture absorption characteristics of the fiber. The moisture content of PFs was evaluated by cutting them into 5-10 mm lengths and drying them in an oven at 103°C for 4 hours before placing them in a desiccator for 24 hours. The calculation of moisture contents is analogous, normal weight loss methods were used. Weighed PFs were dried in an oven at 105°C for 4 hours, then chilled in a desiccator for 10-15 minutes and left until the weight of fibers reached constant. The moisture content in PFs was determined by using formula 2 [2, 6].

$$\%Mc = \frac{W_{fb} - W_{fa}}{W_{fb}} \times 100 \quad (4)$$

where Mc is the moisture content, W_{fb} (g) is the weight before putting in oven, and W_{fa} is the weight after putting in oven.

2.4.3. FTIR

To detect the distinctive functional groups, a Perkin Elmer Spectrum FTIR spectrometer (model Frontier) was employed by delivering infrared light via the sample fibers and co-adding 32 scans at 8 cm^{-1} resolutions within the $4000\text{--}450\text{ cm}^{-1}$ range with a resolution of 4 cm^{-1} [14]. Following that, the FTIR spectra of raw and processed PFs were studied.

2.4.4. Chemical Content

The chemical composition influences fiber characteristics. TAPPI Standard T 264 technique [14] was used to assess the raw as well as NaOH, and KOH treated fibers.

2.4.5. XRD

The crystallization of PFS fibers was examined using XRD analysis before and after alkali treatment, while the PHILIPS X-ray diffractometer was used to evaluate the powdered cured fiber (model PW3050). With a target monochromatic radiation of Cu K, the diffractometer was set to run at 30 mA current, 40 kV voltage, and 30 mA current. Equation 5 was used to calculate the cured PFs's crystallinity index [3].

$$CI = \frac{H_{(002)} - H_{(101)}}{H_{(101)}} \quad (5)$$

where CI : is the crystallinity index of the PFs, $H_{(002)}$ denotes the maximum height of the crystalline fraction at 2θ ($22.07^\circ - 22.31^\circ$), and $H_{(101)}$ is the smaller peak of the amorphous fraction at $2\theta = 18.23^\circ$.

2.4.6. Single PFs Tensile Test

The tensile strength of PFs raw, NaOH treated, and KOH treated PFs was tested using a universal testing machine (UTM) brand INSTRON 1390. The test was carried out in line with ASTM D3379-7. To determine the accuracy of the PFs test results, at room temperature, ten samples of each raw and alkali-treated fiber were tested at a loading rate of 2.5 mm/min . The average tensile strength of a single fiber is computed by using Equation 6 [9].

$$\sigma_f = \frac{4F}{\pi d^2} \quad (6)$$

where σ_f denotes tensile strength, F denotes the maximum tensile force required to break the PFs, and d denotes average diameter.

2.4.7. SEM morphology

The surface morphology or bonding of shattered materials used in tensile tests was characterized using SEM with a JEOL Model JSM - 840A. To investigate the bonding and interior structural changes, as well as to improve sample

conductivity, the surfaces were coated with a thin layer of gold sputtering using a JEOL sputter ion coater, while the morphology was investigated using SEM at 10 kV.

2.4.8. Thermogravimetric analysis (TGA)

TG analysis was utilized to study the thermal durability of the PFs by monitoring weight change over time at a steady temperature range of 25°C to 600°C using a thermogravimetric analyzer (NETZSCH STA 2500).

3. Result discussions

3.1. Fiber density and diameter analysis

Table 2 shows that the diameter was reduced by 25% and 18.27%, respectively after the treatment with 5% NaOH or 5% KOH compared to raw PFs. This is due to impurities being removed from PFs surfaces. Raw PFs were observed to have a lower density than treated fibers. The elimination of lower density sections such as lignin and hemicellulose caused the densities to rise. A higher density suggests that the fibers contain more cellulose. These PFs have a higher density than 8% treated corn husk fiber (0.61 g/cm^3) [3] but lower than glass (2.54 g/cm^3) [22].

3.2. Moisture content analysis

The NaOH and KOH treatments reduced the moisture content of the PFs, as demonstrated in Table 2. The moisture absorption of raw PFs namely 7.18% is higher than that of NaOH and KOH treated fibers of 6.87% and 6.46%, respectively. The structure's hydrogen bond is broken down by alkali treatment, which improves matrix interlocking by reducing the hydrophilic hydroxyl groups in the fiber [7, 23].

3.3. FTIR analysis

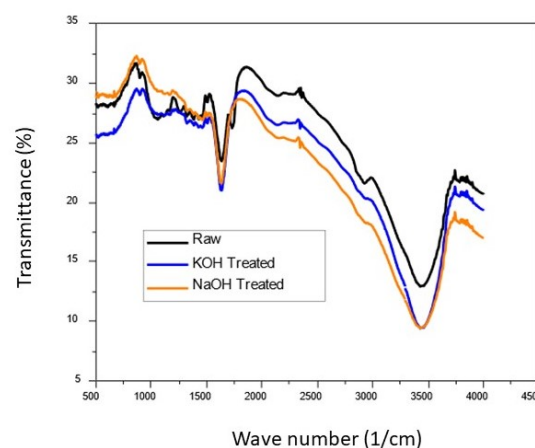
The chemical treatment was utilized to clear the PFs surface of hemicellulose, lignin, and other impurities, whilst FTIR was used to analyze the effects of alkali treatment on fiber chemical processes. Fig. 4 depicts the complete infrared pattern of PFs samples. A spectrum recorded between 4000 cm^{-1} to 400 cm^{-1} corresponds to hydrogen bonding alcohols or OH molecules extending from cellulose, hemicellulose, and lignin. The C-H bond, which is common in alkane groups, was found at the broadband of $3400\text{--}2850\text{ cm}^{-1}$. The absorption was observed at a wave number of 3440 cm^{-1} when the fiber was treated with NaOH and KOH, which is connected to the C-H strain vibration in cellulose and hemicellulose [14, 24]. Peaks at 1727 cm^{-1} were attributed to the C=O bending vibration of OH groups in hemicellulose compounds for raw fibers, as seen in Fig. 4. In the case of PFs treated with 5% NaOH and 5% KOH, the

Table 1. PFS fibers' peak location and chemical assignment group.

Wavenumber (cm ⁻¹)	Raw	NaOH treated	KOH Treated	Assignments
3473	3440	3440	3440	Stretching -cellulose's O-H vibration and hydrogen bonding of hydroxyl groups.
2958	2941	2941	2957	C-H stretching vibration of cellulose and hemicellulose components on hemicellulose/alkyl C-H stretching
2359	2309	2309	2343	C-C alkynes group
1727	—	—	—	CO stretching of Hemicellulose C=O stretching of carboxylic acid and ester group of hemicellulose
1645	1628	1628	1628	CO stretching of lignin
1529	1512	1512	1462	Lignin/ aromatic C=C stretching in lignin
1063	—	—	—	Lignin, hemicellulose, cellulose C-O stretching vibration on cellulose.
847	897	897	847	C-H bond of aromatic hydrogen from lignin compound
465	414	414	531	COOH bending band and the CH ₂ symmetric bending

strength of their peaks was not apparent. The presence of hemicellulose compounds in the fibers was reduced after alkali treatment. The positions of the peaks, as well as the chemical assignment groups of the PFs, are shown in Table 1.

The most prevalent chemical compositions of fibers that affect chemical, physical, and tensile strength features are cellulose, lignin, hemicellulose, and wax. Table 3 illustrates the chemical compositions of raw, as well as NaOH, and KOH-treated PFs. The cellulosic fiber swelled due to alkali treatments, this also removed hemicellulose, lignin, and other impurities from the surface of the PFs. A higher cellulose percentage improves mechanical properties, while a high hemicellulose content reduces fiber strength by promoting cellulosic microfibril disintegration [14].

**Fig. 4.** FTIR of PFs before and after NaOH and KOH treatments.

3.4. Chemical Properties analysis of PFs

The elimination of the majority of the hemicellulose components has an effect on the PFs properties, and morphology. The amount of lignin in the NaOH and KOH-treated fiber was reduced by 19.09% and 16.687%, respectively compared to the PFs raw. Furthermore, Table 3 shows that treated PFs had significantly higher cellulose content than the raw. This wide range is presumably because PFs in nature contain more cellulose than hemicellulose, lignin, and other compounds. As indicated in Table 3, treatment with NaOH and KOH increases the content of cellulose.

3.5. XRD analysis

Fig. 5 shows the XRD spectra of raw, as well as the alkali treated PFs. The curve for the samples presents two pri-


Table 2. Raw and alkali-treated PFs' density, moisture content, and diameter.

Sample	Density (g/cm ³)	Moisture content (%)	Diameter (mm)
raw	0.9 ± 0.071	7.18 ± 0.34	0.104 ± 0.03
Treated (5%NaOH)	1.16 ± 0.082	6.87 ± 0.27	0.085 ± 0.021
Treated (5%KOH)	1.09 ± 0.09	6.46 ± 0.38	0.078 ± 0.012


Table 3. Chemical composition of raw, PFs treated NaOH, and PFs treated KOH.

Sample Codes	Composition			
	Cellulose (%)	Lignin (%)	Hemicellulose (%)	Silika (%)
PFs Raw	48.21	24.51	15.84	0.76
Treated (5%NaOH)	52.83	19.83	14.78	0.68
Treated (5%KOH)	50.62	20.42	14.83	0.71

mary sharp peaks with an intense angle at $2\theta = 15.5^\circ$ and 22.53° , respectively, which are part of the crystallography (1 0 1) and (0 0 2). According to Sari et al. [3], a sharp peak angle of 22.53° indicates the presence of type I_β cellulose, but a low peak angle suggests the presence of amorphous compounds from PFs such as wax, lignin, and hemicellulose. The percentage crystallization index of each fiber sample was calculated using equation 5, as illustrated in Fig. 6. In addition, after NaOH and KOH treated, the crystallinity index of raw PFs namely 50.93% increased to 51.34% (fiber treated NaOH) and 55.21% (fiber treated KOH) respectively. Alkaline solutions dissolve wax, hemicellulose, and impurities, as well as non-crystalline components on the fiber surface, culminating in a rise in crystallinity index [17, 24–26].

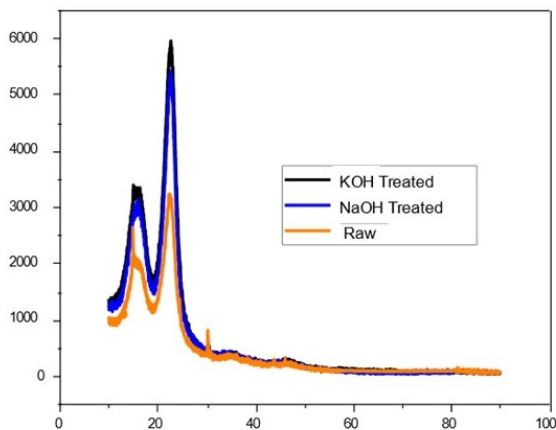**Fig. 5.** XRD spectra of raw and alkali treated PFs.

KOH-treated PFs samples had a higher crystallinity index than pineapple leaves (54% [27], Sisalana Agave (78%) [23]. The increased crystallinity of chemically treated fibers coincides with their higher tensile strength [28]. This suggests that raw PFs, NaOH-treated PFs, and KOH-treated

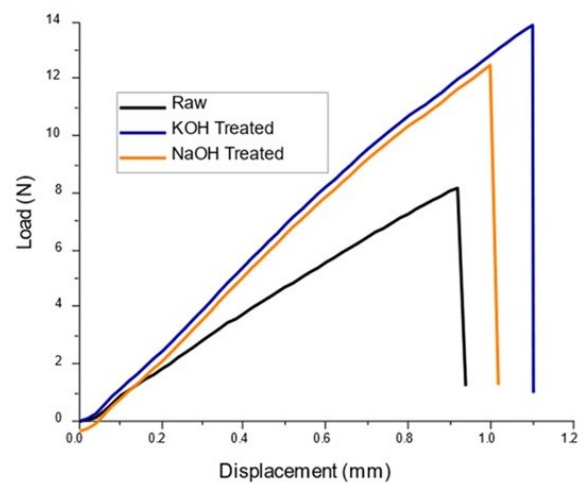**Fig. 6.** Displacement-load of raw and treated PFs.

PFs have the potential to be employed as fillers in composite materials.

3.6. Tensile Strength of PFs

As according to Table 4, the tensile force of PFs treated with NaOH and KOH was increased by 43.27% and 14.18%, respectively, when compared to the PFs raw. The greatest tensile force divided by the surface area of the fibers generates the strength, which is represented in cN/tex. Single PFs treated with NaOH have a stronger toughness than raw or those treated with KOH (Fig. 7). Higher concentrations of NaOH and KOH have been shown to lower fiber toughness [29, 30].

After the alkali treatment, the tensile characteristics of the PFs improved because the cellulose content increased, and the fiber diameter reduced as the hemicellulose and lignin components were lost. With NaOH and KOH treatment, the modulus of elasticity increased by 22.37% and

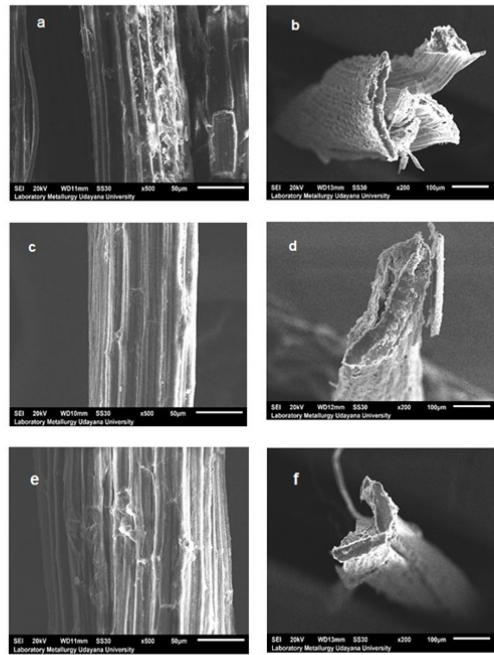


Fig. 7. SEM images of PFs, (a-b) raw, (c-d) NaOH treated and (e-f) KOH treated.

Table 4. Mechanical properties of raw, NaOH and KOH treated PFs.

Sample codes	Tensile Strength (MPa)	Elongation (%)	Modulus of Elasticity (MPa)
Raw	1710.7 ± 76	3.518 ± 0.93	48547 ± 1927
NaOH treated	2450.9 ± 84	4.238 ± 1.08	59405 ± 2085
KOH treated	1953.28 ± 69	4.117 ± 0.9	56304 ± 2108

15.98%, respectively (Table 4). The tensile strength of these PFs is higher than that of coco fiber, with a value of 280.94 MPa [31], and bamboo at 360 MPa [32]. This means that PFs can replace coco and bamboo fiber as a filler in polymer composites.

3.7. SEM analysis

As depicted in Fig. 8a, the raw and alkali-treated surfaces of PFs were covered with fiber impurities such as wax, lignin, or hemicellulose. Meanwhile, due to impurity deposits which preserve the cellulose as well as the presence of a swallow groove and several lumens in the PFs bundle, the fiber cross-sectional surface in Fig. 8b indicates that the fiber surface is still smooth. After the PFs were treated with NaOH as shown in Fig. 8c-d and Fig. 8e-f, the impurities were removed from the surface, thereby making the samples more fibrillar with smaller diameters compared to the raw (Fig. 8(c-d)) or KOH-treated (Fig. 8(e-f)). As a result, the tensile strength increased. The surface of the NaOH-treated PFs is rougher than that of the raw

and KOH-treated PFs. This will allow the PFs treated with NaOH to create interlocking mechanics with a better matrix as a polymer composite reinforcement. Finally, the composite with NaOH-treated fiber reinforcement outperformed the KOH in terms of mechanical parameters.

3.8. TGA analysis

Fig. 8 depicts a three-stage process of changing fiber mass as temperature rises from 28 to 600 °C. The decomposition temperature of PFs treated with NaOH and KOH is greater than the raw types.

Fig. 8 shows that only a tiny change occurred in fiber mass at the first stage, which is between 30 and 150 °C. The process of water or moisture evaporation from the fiber occurs at this step, while the main fiber decomposition occurs at temperatures ranging from 200 °C to 420 °C [33–35]. Hemicellulose compounds decompose at 220 °C to 320 °C, followed by cellulose decomposition. Depending on the degree of composition, the amorphous cellulose portion decomposes first, while the high crystalline type

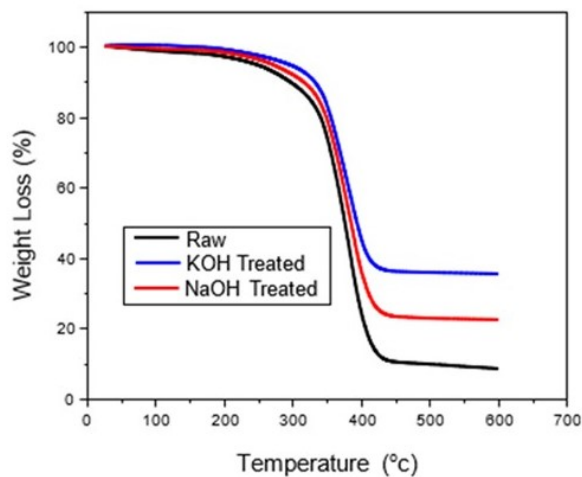


Fig. 8. TGA of *Paederia Foetida* fiber

is relatively stable and requires high temperatures of approximately 300 °C. The decomposition of lignin follows cellulose degradation, and it decomposes slowly from an initial temperature of roughly 150 °C to 900 °C [35–37]. This is because lignin is an extremely hard and inflexible component. Figure 5 also shows that the weight loss of raw fiber is greater than that of fiber after NaOH and KOH treatment because the raw fiber's water content and high hemicellulose content evaporate (see Table 2). Furthermore, the leftover heating composition, including ash and other inorganic components, undergoes the final breakdown [36, 38].

4. Conclusions

As a lightweight and ecologically acceptable composite reinforcement, the characteristics of PFs have been explored by comparing the types of alkaline treatments KOH and NaOH. The color shift was brighter and cleaner due to the alkaline treatment, while the dissolving of wax, lignin, and hemicellulose of fibers reduced moisture content and fiber diameter. Additionally, the density of PFs tends to rise as the fiber's cellulose concentration increases. After NaOH and KOH treatment, PFS's tensile strength and crystallinity index increased from 1710.7 MPa to 1953.28 MPa and 51.34% and 55.21%, respectively. The thermal stability also improved, while the shape of the fiber appeared rougher due to the component disintegration. These PFs' mechanical properties have the potential to replace glass fibers and coconut fiber as composite raw materials, particularly in construction applications.

5. Acknowledgment

This research was funded by the Ministry of Education, Culture, Research, and Technology of the Republic of Indonesia with Contract No. 117/E5/PG.02.00.PT/2022 at National competitive basic research grant (PDKN).

References

- [1] A. C. Jadhav, P. Pandit, T. N. Gayatri, P. P. Chavan, and N. C. Jadhav. *Production of Green Composites from Various Sustainable Raw Materials*. Ed. by S. S. Muthu. 2019. DOI: [10.1007/978-981-13-1969-3_1](https://doi.org/10.1007/978-981-13-1969-3_1).
- [2] H. Khalili, M. H. Salim, S.-e. J. Tlemceni, R. Makhoul, F.-Z. S. A. Hassani, H. Ablouh, Z. Kassab, and M. E. Achaby, (2022) "Bio-Nanocomposite Films Based on Cellulose Nanocrystals Filled Polyvinyl Alcohol/Alginate Polymer Blend" *Journal of Fibers and Polymer Composites* 1: 77–96. DOI: [10.55043/jfpc.v1i2.56](https://doi.org/10.55043/jfpc.v1i2.56).
- [3] N. H. Sari, I. N. G. Wardana, Y. S. Irawan, and E. Siswanto, (2018) "Characterization of the Chemical, Physical, and Mechanical Properties of NaOH-treated Natural Cellulosic Fibers from Corn Husks" *Journal of Natural Fibers* 15: 545–558. DOI: [10.1080/15440478.2017.1349707](https://doi.org/10.1080/15440478.2017.1349707).
- [4] S. O. Ismail, E. Akpan, and H. N. Dhakal, (2022) "Review on natural plant fibres and their hybrid composites for structural applications: Recent trends and future perspectives" *Composites Part C: Open Access* 9: 100322. DOI: <https://doi.org/10.1016/j.jcomc.2022.100322>.
- [5] Q. Zhang, Y. Ma, Z. Qi, C. Jia, Y. Yao, and D. Zhang, (2022) "Optimisation on uniformity and compressibility of rapeseed straw cellulose fiber mixtures for straw/mineral hybrid natural fiber composite" *Industrial Crops and Products* 189: 115852. DOI: <https://doi.org/10.1016/j.indcrop.2022.115852>.
- [6] N. H. Sari and Y. A. Padang, (2019) "The characterization tensile and thermal properties of hibiscus tiliaceus cellulose fibers" *IOP Conference Series: Materials Science and Engineering* 539: 012031. DOI: [10.1088/1757-899X/539/1/012031](https://doi.org/10.1088/1757-899X/539/1/012031).
- [7] P. Pandit, M. D. Teli, K. Singha, S. Maiti, and S. Maity, (2021) "Extraction and characterization of novel *Sterculia foetida* fruit shell fibre for composite applications" *Cleaner Engineering and Technology* 4: 100194. DOI: <https://doi.org/10.1016/j.clet.2021.100194>.
- [8] N. H. Sari, A. Rahman, and E. Syafri. *Characterization of Musaceae and Saccharum Officinarum Cellulose Fibers for Composite Application*. 2019.

- [9] N. M. Nurazzi, A. Khalina, M. Chandrasekar, H. A. Aisyah, S. A. Rafiqah, R. A. Ilyas, and Z. M. Hanafee, (2020) "Effect of fiber orientation and fiber loading on the mechanical and thermal properties of sugar palm yarn fiber reinforced unsaturated polyester resin composites" **Polimery** 65: 115–124. DOI: [10.14314/polimery.2020.2.5](https://doi.org/10.14314/polimery.2020.2.5).
- [10] X. Han, L. Ding, Z. Tian, W. Wu, and S. Jiang, (2021) "Extraction and characterization of novel ultrastrong and tough natural cellulosic fiber bundles from manau rattan (*Calamus manan*)" **Industrial Crops and Products** 173: 114103. DOI: <https://doi.org/10.1016/j.indcrop.2021.114103>.
- [11] D. Wahjuningrum, M. Hasanah, R. Departemen, B. Perairan, F. Perikanan, I. Kelautan, and I. P. Bogor, (2016) "Efikasi daun sembukan *Paederia foetida* untuk pencegahan infeksi bakteri *Aeromonas hydrophila* pada ikan nila Efficacy of skunkvine leaves *Paederia foetida* for prevention of *Aeromonas hydrophila* infection on tilapia" **Jurnal Akuakultur Indonesia** 15: 108–116. DOI: [10.19027/jai.15.2.108-116](https://doi.org/10.19027/jai.15.2.108-116).
- [12] N. H. Sari, J. Fajrin, Suteja, and A. Fudholi, (2020) "Characterisation of swellability and compressive and impact strength properties of corn husk fibre composites" **Composites Communications** 18: 49–54. DOI: <https://doi.org/10.1016/j.coco.2020.01.009>.
- [13] B. A. Praveena, A. Buradi, N. Santhosh, V. K. Vasu, J. Hatgundi, and D. Huliya, (2022) "Study on characterization of mechanical, thermal properties, machinability and biodegradability of natural fiber reinforced polymer composites and its Applications, recent developments and future potentials: A comprehensive review" **Materials Today: Proceedings** 52: 1255–1259. DOI: <https://doi.org/10.1016/j.matpr.2021.11.049>.
- [14] A. E. Bekele, H. G. Lemu, and M. G. Jiru, (2022) "Experimental study of physical, chemical and mechanical properties of enset and sisal fibers" **Polymer Testing** 106: 107453. DOI: <https://doi.org/10.1016/j.polymertesting.2021.107453>.
- [15] N. Shanmugasundaram, I. Rajendran, and T. Ramkumar, (2018) "Static, dynamic mechanical and thermal properties of untreated and alkali treated mulberry fiber reinforced polyester composites" **Polymer Composites** 39: E1908–E1919. DOI: <https://doi.org/10.1002/pc.24890>.
- [16] M. Khan, S. Rahamathbaba, M. A. Mateen, D. V. R. Shankar, and M. M. Hussain, (2019) "Effect of NaOH treatment on mechanical strength of banana/epoxy laminates" **Polymers from Renewable Resources** 10: 19–26. DOI: [10.1177/2041247919863626](https://doi.org/10.1177/2041247919863626).
- [17] N. A. F. M. Nasir, J. Jamaluddin, Z. Zainudin, M. M. Busheri, N. Adrus, F. S. S. Azim, and R. Hasham, (2020) "The effect of alkaline treatment onto physical, thermal, mechanical and chemical properties of Lemba leaves fibres as new resources of biomass" **Pertanika Journal of Science and Technology** 28: 1531–1547. DOI: [10.47836/pjst.28.4.21](https://doi.org/10.47836/pjst.28.4.21).
- [18] S. Maity, P. Paul, K. Singha, D. P. Gon, and M. Singha, (2012) "A Review on Jute Nonwovens: Manufacturing, Properties and Applications Engineering Fibers for Fog Harvesting and Interfacial Solar Water Purification View project Electro-conductive textiles View project A Review on Jute Nonwovens: Manufacturing, Properties and Applications" **International Journal of Textile Science** 2012: 36–43. DOI: [10.5923/j.textile.20120105.02](https://doi.org/10.5923/j.textile.20120105.02).
- [19] R. Liu, H. Xiao, S. D. Pang, J. Geng, and H. Yang, (2020) "Application of *Sterculia foetida* petiole wastes in lightweight pervious concrete" **Journal of Cleaner Production** 246: 118972. DOI: <https://doi.org/10.1016/j.jclepro.2019.118972>.
- [20] A. Amiri, Z. Triplett, A. Moreira, N. Brezinka, M. Alcock, and C. A. Ulven, (2017) "Standard density measurement method development for flax fiber" **Industrial Crops and Products** 96: 196–202. DOI: <https://doi.org/10.1016/j.indcrop.2016.11.060>.
- [21] A. Bazargan, T. Gebreegziabher, C.-W. Hui, and G. McKay, (2014) "The effect of alkali treatment on rice husk moisture content and drying kinetics" **Biomass and Bioenergy** 70: 468–475. DOI: <https://doi.org/10.1016/j.biombioe.2014.08.018>.
- [22] O. Faruk, A. K. Bledzki, H.-P. Fink, and M. Sain, (2012) "Biocomposites reinforced with natural fibers: 2000–2010" **Progress in Polymer Science** 37: 1552–1596. DOI: <https://doi.org/10.1016/j.progpolymsci.2012.04.003>.
- [23] B. S. L. Brito, F. V. Pereira, J.-L. Putaux, and B. Jean, (2012) "Preparation, morphology and structure of cellulose nanocrystals from bamboo fibers" **Cellulose** 19: 1527–1536. DOI: [10.1007/s10570-012-9738-9](https://doi.org/10.1007/s10570-012-9738-9).
- [24] S. G. Subramanian, R. Rajkumar, and T. Ramkumar, (2021) "Characterization of Natural Cellulosic Fiber from *Cereus Hildmannianus*" **Journal of Natural Fibers** 18: 343–354. DOI: [10.1080/15440478.2019.1623744](https://doi.org/10.1080/15440478.2019.1623744).

- [25] K. H. Reddy, R. M. Reddy, M. Ramesh, D. M. Krishnudu, B. M. Reddy, and H. R. Rao, (2021) "Impact of Alkali Treatment on Characterization of Tapsi (*Sterculia Urens*) Natural Bark Fiber Reinforced Polymer Composites" **Journal of Natural Fibers** 18: 378–389. DOI: [10.1080/15440478.2019.1623747](https://doi.org/10.1080/15440478.2019.1623747).
- [26] G. M. A. Khan, M. S. A. Shams, M. R. Kabir, M. A. Gafur, M. Terano, and M. S. Alam, (2013) "Influence of chemical treatment on the properties of banana stem fiber and banana stem fiber/coir hybrid fiber reinforced maleic anhydride grafted polypropylene/low-density polyethylene composites" **Journal of Applied Polymer Science** 128: 1020–1029. DOI: <https://doi.org/10.1002/app.38197>.
- [27] B. M. Cherian, A. L. Leão, S. F. de Souza, S. Thomas, L. A. Pothan, and M. Kottaisamy, (2010) "Isolation of nanocellulose from pineapple leaf fibres by steam explosion" **Carbohydrate Polymers** 81: 720–725. DOI: <https://doi.org/10.1016/j.carbpol.2010.03.046>.
- [28] R. A. Ilyas, S. M. Sapuan, M. R. Ishak, and E. S. Zainudin, (2017) "Effect of delignification on the physical, thermal, chemical, and structural properties of sugar palm fibre" **BioResources** 12: 8734–8754. DOI: [10.15376/biores.12.4.8734-8754](https://doi.org/10.15376/biores.12.4.8734-8754).
- [29] M. Truong, W. Zhong, S. Boyko, and M. Alcock, (2009) "A comparative study on natural fibre density measurement" **The Journal of The Textile Institute** 100: 525–529. DOI: [10.1080/00405000801997595](https://doi.org/10.1080/00405000801997595).
- [30] M. V. Maheshwaran, N. R. J. Hyness, P. Senthama-raikannan, S. S. Saravanakumar, and M. R. Sanjay, (2018) "Characterization of natural cellulosic fiber from *Epipremnum aureum* stem" **Journal of Natural Fibers** 15: 789–798. DOI: [10.1080/15440478.2017.1364205](https://doi.org/10.1080/15440478.2017.1364205).
- [31] M. Arsyad, (2017) "Effect of Alkali Treatment on The Coconut Fiber Surface" **ARPN Journal of Engineering and Applied Sciences** 12:
- [32] Y. Wu, Y. Zheng, F. Yang, and L. Yang, (2021) "Preparation process and characterization of mechanical properties of twisted bamboo spun fiber bundles" **Journal of Materials Research and Technology** 14: 2131–2139. DOI: <https://doi.org/10.1016/j.jmrt.2021.07.080>.
- [33] M. N. Norizan, K. Abdan, M. S. Salit, and R. Mohamed, (2017) "Physical, mechanical and thermal properties of sugar palm yarn fibre loading on reinforced unsaturated polyester composites." **Journal of Physical Science** 28(3):
- [34] D. Atalie and R. K. Gideon, (2018) "Extraction and characterization of Ethiopian palm leaf fibers" **Research Journal of Textile and Apparel** 22: 15–25. DOI: [10.1108/RJTA-06-2017-0035](https://doi.org/10.1108/RJTA-06-2017-0035).
- [35] D. Watkins, M. Nuruddin, M. Hosur, A. Tcherbi-Narteh, and S. Jeelani, (2015) "Extraction and characterization of lignin from different biomass resources" **Journal of Materials Research and Technology** 4: 26–32. DOI: <https://doi.org/10.1016/j.jmrt.2014.10.009>.
- [36] J. Sahari, S. M. Sapuan, E. S. Zainudin, and M. A. Maleque, (2013) "Mechanical and thermal properties of environmentally friendly composites derived from sugar palm tree" **Materials Design** 49: 285–289. DOI: <https://doi.org/10.1016/j.matdes.2013.01.048>.
- [37] A. Oushabi, S. Sair, F. O. Hassani, Y. Abboud, O. Tanane, and A. E. Bouari, (2017) "The effect of alkali treatment on mechanical, morphological and thermal properties of date palm fibers (DPFs): Study of the interface of DPF–Polyurethane composite" **South African Journal of Chemical Engineering** 23: 116–123. DOI: <https://doi.org/10.1016/j.sajce.2017.04.005>.
- [38] R. Vijay, A. Vinod, D. L. Singaravelu, M. R. Sanjay, and S. Siengchin, (2021) "Characterization of chemical treated and untreated natural fibers from *Penisetum orientale* grass- A potential reinforcement for lightweight polymeric applications" **International Journal of Lightweight Materials and Manufacture** 4: 43–49. DOI: <https://doi.org/10.1016/j.ijlmm.2020.06.008>.

Comprehensive Characterization Of Novel Cellulose Fiber From *Paederia Foetida* and Its Modification For Sustainable Composites Application

Nasmi Herlina Sari^{1*}, Edi Syafri², Suteja¹, Widya Fatriasari³, and Azizatul Karimah³

¹ Department of Mechanical Engineering, Faculty of Engineering, University of Mataram, Mataram, West Nusa Tenggara 83125, Indonesia

² Department of Agricultural Technology, Politeknik Pertanian Negeri Payakumbuh, Payakumbuh, West Sumatera 26271, Indonesia

³ Research Center for Biomass and Bioproducts, National Research and Innovation Agency (BRIN), Jl. Raya Bogor Km 46, Cibinong, Bogor 16911, Indonesia

* Corresponding author. E-mail: n.herlinasari@unram.ac.id

Received: Sep. 20, 2022; Accepted: Nov. 28, 2022

Fiber derived from the plant *Paederia Foetida* stems (PF) is a novel natural fiber with the capacity to replace glass fibers in composite reinforcement. The technique of modifying the fiber surface with NaOH and KOH is simple and straightforward, generating properties that differ from the raw fiber. Therefore, this study aims to investigate the effects of NaOH and KOH treatments on the surface of *Paederia foetida* fiber (PFs) in relation to the physical, crystal structure, functional groups, tensile strength, thermal and morphological properties compared to raw PFs. The raw fiber was obtained by soaking the PFs rods in water for 10 days, followed by surface treatment with a solution of NaOH and KOH. The results showed that compared to raw fiber, after NaOH dan KOH treated PFs, the diameter and moisture content of the PFs decreased, while the tensile strength increased significantly by 43.27%, and good thermal stability. The highest crystallinity index was obtained from KOH-treated PFs of 79.685%. According to the functional groups in the FTIR observations, NaOH treatment was found to be more effective in removing lignin and hemicellulose components, as well as increasing cellulose compounds in the fiber. The surface morphology was found to be rougher with the loss of impurities after NaOH treatment. Based on the results, raw, NaOH and KOH-treated PFs have the potential to be used as reinforcement for lightweight composite and alternative materials to replace glass fiber and coconut fiber in construction applications.

Keywords: Chemical; KOH; mechanical properties; NaOH; *Paederia foetida* fiber (PFs); physical properties

© The Author(s). This is an open-access article distributed under the terms of the [Creative Commons Attribution License \(CC BY 4.0\)](https://creativecommons.org/licenses/by/4.0/), which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are cited.

[http://dx.doi.org/10.6180/jase.202310_26\(10\).0005](http://dx.doi.org/10.6180/jase.202310_26(10).0005)

1. Introduction

Nature has provided various renewable and environmentally friendly resources that have many potentials uses for textile fibers and composite materials. Natural fibers can be produced from any part of the plant and used in a wide range of applications, including fibers and textiles for composite applications [1–5]. In recent decades, new natural fibers with their best properties have been investigated and characterized such as corn husk fiber [1], *Juncus* plant [2],

Hibiscus tiliceaus fiber [6], *Sterculia foetida* fruit shell fiber [5, 7], *Musaceae* and *Saccharum officinarum* Cellulose Fibers [8], etc. Furthermore, the lignocellulosic natural fiber is known to have strength and stiffness properties comparable to glass fiber, as well as low density, and non-abrasive [1, 9, 10]. These unique traits and properties have created opportunities for the investigation and development of various natural fibers.

One source of natural fiber that has not been utilized optimally is *Paederia foetida* (PF) which grows convoluted

vines, as well as forms shrubs and annuals. Furthermore, PF leaves belong to the *Rubiceae* tribe, have soft stems, and are used for climbing trees. They are only half a centimeter in diameter but can reach 10 m in length. Several investigations have been conducted on the PF plant in relation to the use of drugs in the health sector, such as anti-rheumatic, analgesics, mucolytics, appetite enhancers, antibiotics, anti-inflammatory, cough medicines or anti-tussive, and diarrhea medication [11]. However, there is no information related to the use of fiber from the PF plant as a filler for composite materials. The abundant and eco-friendly fiber sources from this plant need to be developed to achieve excellent mechanical, physical, and thermal durability, as well as for wider applications.

Several investigations on the reinforcing of natural fibers in polymer composite materials to obtain desired qualities have been conducted. However, the developed composites often experience mechanical failures such as fiber pullout and debonding with the matrix. This failure is presumably due to the poor adhesion between hydrophobic (polymer) and hydrophilic (fibers), culminating in poor mechanical properties [12, 13]. Fortunately, Natural fibers' hydrophilic qualities can be lowered chemically by treating them with NaOH, silane, KOH, and peroxide [6, 8, 14]. Sari et al. [3] reported that the tensile strength of a single cornhusk fiber was enhanced to 368.25 MPa after being modified with NaOH from 0.5 to 8% for 2 hours. Furthermore, Shanmugasundaram & Ramkumar [15] stated that the cellulose content of betel leaf fiber of 57.49% can be increased to 68.54% after treatment with 5% NaOH. Sari and Padang, [6] also reported that the tensile strength of *T. hibiscus* fiber after treatment with 8% KOH reached 5144.9 MPa, while the surface of the fiber became cleaner, rougher, and fibrillar. Khan et al. [16] mentioned that banana fiber improved the mechanical properties after the treatment with NaOH solution. It was also discovered that the epoxy composite with banana fiber reinforcement treated with 4.5% NaOH had the greatest improvement in both compressive and tensile strength, with 24.2% and 34% increases, respectively. The optimal epoxy composite strength was obtained at 25.4 MPa or increased by 38% after banana fiber was treated with 6.5% NaOH. Mat Nasir et al. [17] also reported that after being treated with 6-10 wt% sodium hydroxide (NaOH) solution for 24 hours, Lemba Leaves Fibers (LeLeF) have fiber diameters in the range of 191.37 μm - 36.81 μm , and tensile properties in the range of 14.45 - 511.10 MPa, where the resulting properties are better than raw fiber. The mechanical properties and thermal stability of the fiber after NaOH treatment are superior to raw catfish fiber. Maity et al. [18] investigated the characteristics and uses of jute

and nonwoven-based composites. Meanwhile, Liu et al. [19] gathered *Sterculia* and *Foetida* plant stalk debris and slices it long and short, with an average length of around 38 mm and 16 mm, to make environmentally sustainable light translucent concrete. Furthermore, alkaline treatment has been shown to increase the moisture retention of biomass while decreasing the activation energy of rice husks. While it is known that sample pre-treatment increases the drying rate and effective diffusivity of rice husks [20]. This previous study shows that the properties of new natural fibers need to be investigated and developed. The unique properties of different, abundant, and environmentally friendly natural fibers need to be considered to encounter composite reinforcing materials. The modification of natural fibers also needs to be investigated to ensure the best properties which can provide added value to natural fibers.

Therefore, the purpose of this study was to provide detailed information on the extraction and evaluation of new natural fibers from the fiber stems of the plant *Paederia foetida* (PFs). The characteristics of the fiber were investigated through changes in morphology, tensile strength, thermal resistance, crystallinity index, and functional groups. The properties of the raw materials used will be compared to those of the fiber post-treatment with NaOH and KOH.

2. Experimental program

2.1. Materials

Paederia foetida plant in Fig. 1a was collected from Batukliang, Lombok, Indonesia, the stems were separated from the leaves manually, then sliced to lengths of 150 mm (Fig. 1b). Furthermore, a solution of 5% sodium hydroxide (5% NaOH) and 5% potassium hydroxide (5% KOH) was used as alkali treatment. It was obtained from the Biochemistry Laboratory, Faculty of Food Technology and Agricultural Products, University of Mataram.

2.2. Extraction of *Paederia foetida* fiber

The PF were soaked for 10 days in fresh water (Fig. 1c) to allow them to rot, then, the fibers from the rods were removed using a plastic comb to maintain a uniform diameter, subsequently, they were air-dried and prepared to be tested (Fig. 1d).

2.3. Alkali treatment of PFs

The PFs were immersed in 5% NaOH and 5% KOH alkaline solutions for 2 h at room temperature of 28 oC. Next, they were washed with distilled water four times to remove the remaining alkaline solution, followed by drying in the sun.



Fig. 1. *Paederia foetida*, PF, (a) plant, (b) selection of PF stems, (c) Soaking PF in water, (d) Extracting fiber from PF stems.

Below is the reaction scheme [1, 8].



Following that, the PFs were placed in a dry plastic container with a humidity of 20%; Fig. 2 depicts the alkaline treatment method for PFs. Raw fibers as well as those treated with NaOH, and KOH are shown in Fig. 3.

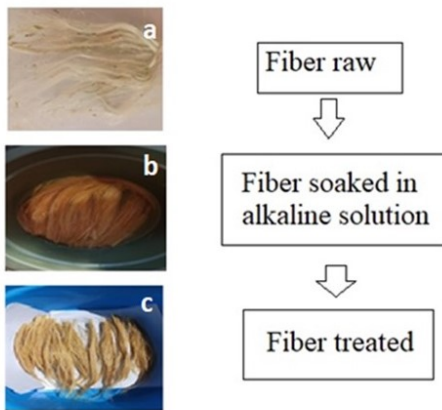


Fig. 2. Alkaline treatment process of PFs (a) fiber raw, (b) alkalization, and (c) dry PFs.

2.4. Characterization

2.4.1. Fiber density and diameter

A single PF sample was cut into small splices and placed on a microscope slide, then the raw and alkali-treated fiber diameters were measured using optical microscopy. A randomly selected 10 samples were measured at five locations along the length, and the average diameter value was reported.



Fig. 3. PFs (a) raw, (b) KOH treated dan (c) NaOH treated.

Furthermore, the buoyancy force was calculated by weighing PFs first in air and then in distilled water. The weighing was done using an analytical balance with a resolution of 0.001 g and was adapted for suspension weighing using a stainless-steel wire with a diameter of approximately 0.4 mm. By dividing the liquid density by the buoyancy force, sample volume was calculated. The density ρ_f was calculated by dividing the sample weight in air by the volume of the sample [1, 14].

$$\rho_f = \frac{(m_3 - m_1)}{(m_3 - m_1) - (m_4 - m_2)} \rho_w \quad (3)$$

where ρ_f is the fiber density (g/cm^3), and m_1 and m_2 are the weights of suspension wire in air and liquid, respectively. m_3 and m_4 represent the weight of the wire plus the sample weight in air and liquid (g), respectively. $\rho_w = 0.998 \text{ g}/\text{cm}^3$ (standard density of distilled water). All densities were measured using a Mettler Toledo measurement kit at $23 \pm 0.2^\circ\text{C}$ [14].

2.4.2. Moisture content

Water absorption has an impact on the physical properties of composites as well as the PFs-matrix interface [21]. The lowered hydrophilic hydroxyl groups increased the moisture absorption characteristics of the fiber. The moisture content of PFs was evaluated by cutting them into 5-10 mm lengths and drying them in an oven at 103°C for 4 hours before placing them in a desiccator for 24 hours. The calculation of moisture contents is analogous, normal weight loss methods were used. Weighed PFs were dried in an oven at 105°C for 4 hours, then chilled in a desiccator for 10-15 minutes and left until the weight of fibers reached constant. The moisture content in PFs was determined by using formula 2 [2, 6].

$$\%Mc = \frac{W_{fb} - W_{fa}}{W_{fb}} \times 100 \quad (4)$$

where Mc is the moisture content, W_{fb} (g) is the weight before putting in oven, and W_{fa} is the weight after putting in oven.

2.4.3. FTIR

To detect the distinctive functional groups, a Perkin Elmer Spectrum FTIR spectrometer (model Frontier) was employed by delivering infrared light via the sample fibers and co-adding 32 scans at 8 cm^{-1} resolutions within the $4000\text{--}450\text{ cm}^{-1}$ range with a resolution of 4 cm^{-1} [14]. Following that, the FTIR spectra of raw and processed PFs were studied.

2.4.4. Chemical Content

The chemical composition influences fiber characteristics. TAPPI Standard T 264 technique [14] was used to assess the raw as well as NaOH, and KOH treated fibers.

2.4.5. XRD

The crystallization of PFS fibers was examined using XRD analysis before and after alkali treatment, while the PHILIPS X-ray diffractometer was used to evaluate the powdered cured fiber (model PW3050). With a target monochromatic radiation of Cu K, the diffractometer was set to run at 30 mA current, 40 kV voltage, and 30 mA current. Equation 5 was used to calculate the cured PFs's crystallinity index [3].

$$CI = \frac{H_{(002)} - H_{(101)}}{H_{(101)}} \quad (5)$$

where CI : is the crystallinity index of the PFs, $H_{(002)}$ denotes the maximum height of the crystalline fraction at 2θ ($22.07^\circ - 22.31^\circ$), and $H_{(101)}$ is the smaller peak of the amorphous fraction at $2\theta = 18.23^\circ$.

2.4.6. Single PFs Tensile Test

The tensile strength of PFs raw, NaOH treated, and KOH treated PFs was tested using a universal testing machine (UTM) brand INSTRON 1390. The test was carried out in line with ASTM D3379-7. To determine the accuracy of the PFs test results, at room temperature, ten samples of each raw and alkali-treated fiber were tested at a loading rate of 2.5 mm/min . The average tensile strength of a single fiber is computed by using Equation 6 [9].

$$\sigma_f = \frac{4F}{\pi d^2} \quad (6)$$

where σ_f denotes tensile strength, F denotes the maximum tensile force required to break the PFs, and d denotes average diameter.

2.4.7. SEM morphology

The surface morphology or bonding of shattered materials used in tensile tests was characterized using SEM with a JEOL Model JSM - 840A. To investigate the bonding and interior structural changes, as well as to improve sample

conductivity, the surfaces were coated with a thin layer of gold sputtering using a JEOL sputter ion coater, while the morphology was investigated using SEM at 10 kV.

2.4.8. Thermogravimetric analysis (TGA)

TG analysis was utilized to study the thermal durability of the PFs by monitoring weight change over time at a steady temperature range of 25°C to 600°C using a thermogravimetric analyzer (NETZSCH STA 2500).

3. Result discussions

3.1. Fiber density and diameter analysis

Table 2 shows that the diameter was reduced by 25% and 18.27%, respectively after the treatment with 5% NaOH or 5% KOH compared to raw PFs. This is due to impurities being removed from PFs surfaces. Raw PFs were observed to have a lower density than treated fibers. The elimination of lower density sections such as lignin and hemicellulose caused the densities to rise. A higher density suggests that the fibers contain more cellulose. These PFs have a higher density than 8% treated corn husk fiber (0.61 g/cm^3) [3] but lower than glass (2.54 g/cm^3) [22].

3.2. Moisture content analysis

The NaOH and KOH treatments reduced the moisture content of the PFs, as demonstrated in Table 2. The moisture absorption of raw PFs namely 7.18% is higher than that of NaOH and KOH treated fibers of 6.87% and 6.46%, respectively. The structure's hydrogen bond is broken down by alkali treatment, which improves matrix interlocking by reducing the hydrophilic hydroxyl groups in the fiber [7, 23].

3.3. FTIR analysis

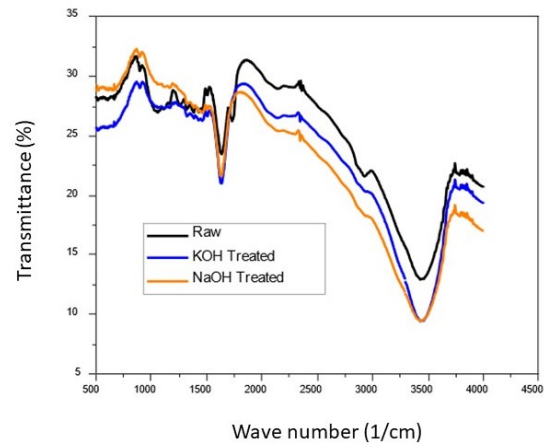
The chemical treatment was utilized to clear the PFs surface of hemicellulose, lignin, and other impurities, whilst FTIR was used to analyze the effects of alkali treatment on fiber chemical processes. Fig. 4 depicts the complete infrared pattern of PFs samples. A spectrum recorded between 4000 cm^{-1} to 400 cm^{-1} corresponds to hydrogen bonding alcohols or OH molecules extending from cellulose, hemicellulose, and lignin. The C-H bond, which is common in alkane groups, was found at the broadband of $3400\text{--}2850\text{ cm}^{-1}$. The absorption was observed at a wave number of 3440 cm^{-1} when the fiber was treated with NaOH and KOH, which is connected to the C-H strain vibration in cellulose and hemicellulose [14, 24]. Peaks at 1727 cm^{-1} were attributed to the C=O bending vibration of OH groups in hemicellulose compounds for raw fibers, as seen in Fig. 4. In the case of PFs treated with 5% NaOH and 5% KOH, the

Table 1. PFS fibers' peak location and chemical assignment group.

Wavenumber (cm ⁻¹)	Raw	NaOH treated	KOH Treated	Assignments
3473	3440	3440	3440	Stretching -cellulose's O-H vibration and hydrogen bonding of hydroxyl groups.
2958	2941	2941	2957	C-H stretching vibration of cellulose and hemicellulose components on hemicellulose/alkyl C-H stretching
2359	2309	2309	2343	C-C alkynes group
1727	—	—	—	CO stretching of Hemicellulose C=O stretching of carboxylic acid and ester group of hemicellulose
1645	1628	1628	1628	CO stretching of lignin
1529	1512	1512	1462	Lignin/ aromatic C=C stretching in lignin
1063	—	—	—	Lignin, hemicellulose, cellulose C-O stretching vibration on cellulose.
847	897	897	847	C-H bond of aromatic hydrogen from lignin compound
465	414	414	531	COOH bending band and the CH ₂ symmetric bending

strength of their peaks was not apparent. The presence of hemicellulose compounds in the fibers was reduced after alkali treatment. The positions of the peaks, as well as the chemical assignment groups of the PFs, are shown in Table 1.

The most prevalent chemical compositions of fibers that affect chemical, physical, and tensile strength features are cellulose, lignin, hemicellulose, and wax. Table 3 illustrates the chemical compositions of raw, as well as NaOH, and KOH-treated PFs. The cellulosic fiber swelled due to alkali treatments, this also removed hemicellulose, lignin, and other impurities from the surface of the PFs. A higher cellulose percentage improves mechanical properties, while a high hemicellulose content reduces fiber strength by promoting cellulosic microfibril disintegration [14].

**Fig. 4.** FTIR of PFs before and after NaOH and KOH treatments.

3.4. Chemical Properties analysis of PFs

The elimination of the majority of the hemicellulose components has an effect on the PFs properties, and morphology. The amount of lignin in the NaOH and KOH-treated fiber was reduced by 19.09% and 16.687%, respectively compared to the PFs raw. Furthermore, Table 3 shows that treated PFs had significantly higher cellulose content than the raw. This wide range is presumably because PFs in nature contain more cellulose than hemicellulose, lignin, and other compounds. As indicated in Table 3, treatment with NaOH and KOH increases the content of cellulose.

3.5. XRD analysis

Fig. 5 shows the XRD spectra of raw, as well as the alkali treated PFs. The curve for the samples presents two pri-


Table 2. Raw and alkali-treated PFs' density, moisture content, and diameter.

Sample	Density (g/cm ³)	Moisture content (%)	Diameter (mm)
raw	0.9 ± 0.071	7.18 ± 0.34	0.104 ± 0.03
Treated (5%NaOH)	1.16 ± 0.082	6.87 ± 0.27	0.085 ± 0.021
Treated (5%KOH)	1.09 ± 0.09	6.46 ± 0.38	0.078 ± 0.012


Table 3. Chemical composition of raw, PFs treated NaOH, and PFs treated KOH.

Sample Codes	Composition			
	Cellulose (%)	Lignin (%)	Hemicellulose (%)	Silika (%)
PFs Raw	48.21	24.51	15.84	0.76
Treated (5%NaOH)	52.83	19.83	14.78	0.68
Treated (5%KOH)	50.62	20.42	14.83	0.71

mary sharp peaks with an intense angle at $2\theta = 15.5^\circ$ and 22.53° , respectively, which are part of the crystallography (1 0 1) and (0 0 2). According to Sari et al. [3], a sharp peak angle of 22.53° indicates the presence of type I_β cellulose, but a low peak angle suggests the presence of amorphous compounds from PFs such as wax, lignin, and hemicellulose. The percentage crystallization index of each fiber sample was calculated using equation 5, as illustrated in Fig. 6. In addition, after NaOH and KOH treated, the crystallinity index of raw PFs namely 50.93% increased to 51.34% (fiber treated NaOH) and 55.21% (fiber treated KOH) respectively. Alkaline solutions dissolve wax, hemicellulose, and impurities, as well as non-crystalline components on the fiber surface, culminating in a rise in crystallinity index [17, 24–26].

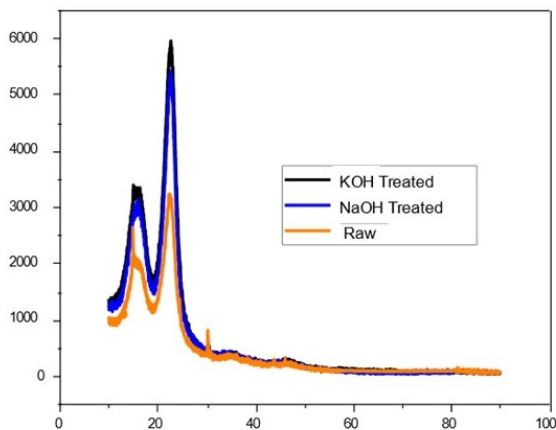**Fig. 5.** XRD spectra of raw and alkali treated PFs.

KOH-treated PFs samples had a higher crystallinity index than pineapple leaves (54% [27], Sisalana Agave (78%) [23]. The increased crystallinity of chemically treated fibers coincides with their higher tensile strength [28]. This suggests that raw PFs, NaOH-treated PFs, and KOH-treated

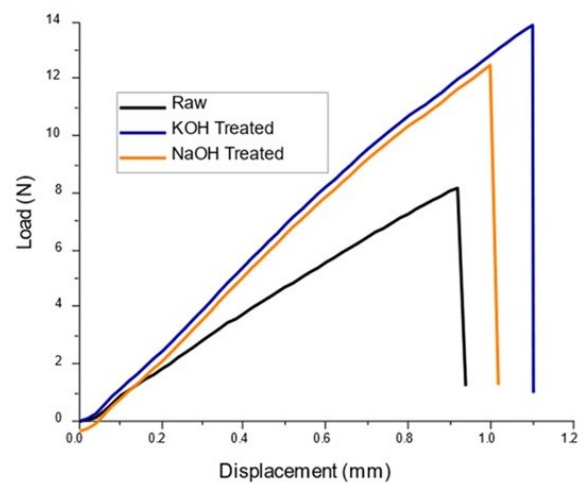**Fig. 6.** Displacement-load of raw and treated PFs.

PFs have the potential to be employed as fillers in composite materials.

3.6. Tensile Strength of PFs

As according to Table 4, the tensile force of PFs treated with NaOH and KOH was increased by 43.27% and 14.18%, respectively, when compared to the PFs raw. The greatest tensile force divided by the surface area of the fibers generates the strength, which is represented in cN/tex. Single PFs treated with NaOH have a stronger toughness than raw or those treated with KOH (Fig. 7). Higher concentrations of NaOH and KOH have been shown to lower fiber toughness [29, 30].

After the alkali treatment, the tensile characteristics of the PFs improved because the cellulose content increased, and the fiber diameter reduced as the hemicellulose and lignin components were lost. With NaOH and KOH treatment, the modulus of elasticity increased by 22.37% and

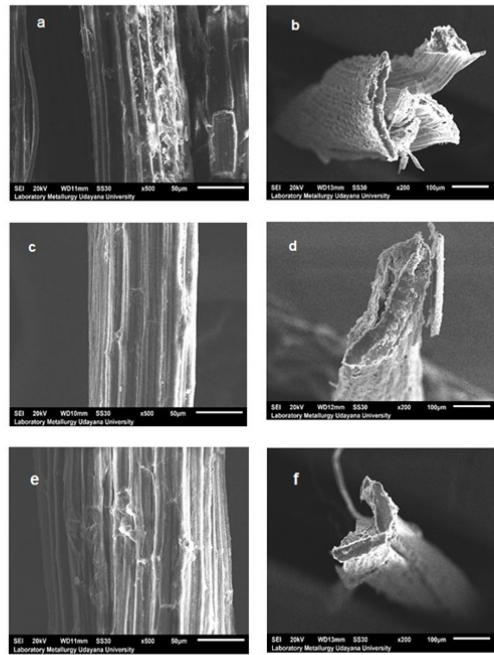


Fig. 7. SEM images of PFs, (a-b) raw, (c-d) NaOH treated and (e-f) KOH treated.

Table 4. Mechanical properties of raw, NaOH and KOH treated PFs.

Sample codes	Tensile Strength (MPa)	Elongation (%)	Modulus of Elasticity (MPa)
Raw	1710.7 ± 76	3.518 ± 0.93	48547 ± 1927
NaOH treated	2450.9 ± 84	4.238 ± 1.08	59405 ± 2085
KOH treated	1953.28 ± 69	4.117 ± 0.9	56304 ± 2108

15.98%, respectively (Table 4). The tensile strength of these PFs is higher than that of coco fiber, with a value of 280.94 MPa [31], and bamboo at 360 MPa [32]. This means that PFs can replace coco and bamboo fiber as a filler in polymer composites.

3.7. SEM analysis

As depicted in Fig. 8a, the raw and alkali-treated surfaces of PFs were covered with fiber impurities such as wax, lignin, or hemicellulose. Meanwhile, due to impurity deposits which preserve the cellulose as well as the presence of a swallow groove and several lumens in the PFs bundle, the fiber cross-sectional surface in Fig. 8b indicates that the fiber surface is still smooth. After the PFs were treated with NaOH as shown in Fig. 8c-d and Fig. 8e-f, the impurities were removed from the surface, thereby making the samples more fibrillar with smaller diameters compared to the raw (Fig. 8(c-d) or KOH-treated (Fig. 8(e-f)), As a result, the tensile strength increased. The surface of the NaOH-treated PFs is rougher than that of the raw

and KOH-treated PFs. This will allow the PFs treated with NaOH to create interlocking mechanics with a better matrix as a polymer composite reinforcement. Finally, the composite with NaOH-treated fiber reinforcement outperformed the KOH in terms of mechanical parameters.

3.8. TGA analysis

Fig. 8 depicts a three-stage process of changing fiber mass as temperature rises from 28 to 600 °C. The decomposition temperature of PFs treated with NaOH and KOH is greater than the raw types.

Fig. 8 shows that only a tiny change occurred in fiber mass at the first stage, which is between 30 and 150 °C. The process of water or moisture evaporation from the fiber occurs at this step, while the main fiber decomposition occurs at temperatures ranging from 200 °C to 420 °C [33–35]. Hemicellulose compounds decompose at 220 °C to 320 °C, followed by cellulose decomposition. Depending on the degree of composition, the amorphous cellulose portion decomposes first, while the high crystalline type

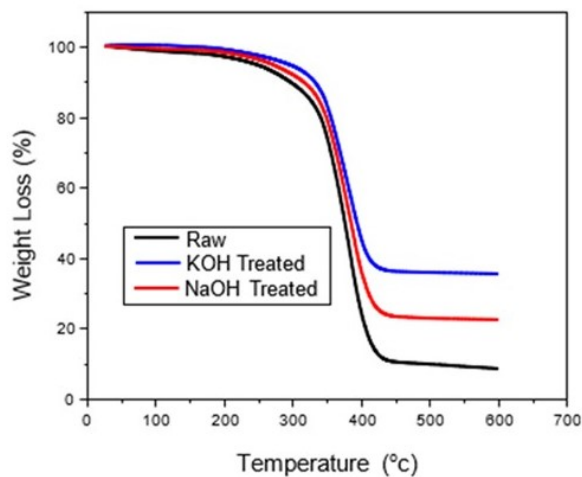


Fig. 8. TGA of *Paederia Foetida* fiber

is relatively stable and requires high temperatures of approximately 300 °C. The decomposition of lignin follows cellulose degradation, and it decomposes slowly from an initial temperature of roughly 150 °C to 900 °C [35–37]. This is because lignin is an extremely hard and inflexible component. Figure 5 also shows that the weight loss of raw fiber is greater than that of fiber after NaOH and KOH treatment because the raw fiber's water content and high hemicellulose content evaporate (see Table 2). Furthermore, the leftover heating composition, including ash and other inorganic components, undergoes the final breakdown [36, 38].

4. Conclusions

As a lightweight and ecologically acceptable composite reinforcement, the characteristics of PFs have been explored by comparing the types of alkaline treatments KOH and NaOH. The color shift was brighter and cleaner due to the alkaline treatment, while the dissolving of wax, lignin, and hemicellulose of fibers reduced moisture content and fiber diameter. Additionally, the density of PFs tends to rise as the fiber's cellulose concentration increases. After NaOH and KOH treatment, PFS's tensile strength and crystallinity index increased from 1710.7 MPa to 1953.28 MPa and 51.34% and 55.21%, respectively. The thermal stability also improved, while the shape of the fiber appeared rougher due to the component disintegration. These PFs' mechanical properties have the potential to replace glass fibers and coconut fiber as composite raw materials, particularly in construction applications.

5. Acknowledgment

This research was funded by the Ministry of Education, Culture, Research, and Technology of the Republic of Indonesia with Contract No. 117/E5/PG.02.00.PT/2022 at National competitive basic research grant (PDKN).

References

- [1] A. C. Jadhav, P. Pandit, T. N. Gayatri, P. P. Chavan, and N. C. Jadhav. *Production of Green Composites from Various Sustainable Raw Materials*. Ed. by S. S. Muthu. 2019. DOI: [10.1007/978-981-13-1969-3_1](https://doi.org/10.1007/978-981-13-1969-3_1).
- [2] H. Khalili, M. H. Salim, S.-e. J. Tlemceni, R. Makhoulouf, F.-Z. S. A. Hassani, H. Ablouh, Z. Kassab, and M. E. Achaby, (2022) "Bio-Nanocomposite Films Based on Cellulose Nanocrystals Filled Polyvinyl Alcohol/Alginate Polymer Blend" *Journal of Fibers and Polymer Composites* 1: 77–96. DOI: [10.55043/jfpc.v1i2.56](https://doi.org/10.55043/jfpc.v1i2.56).
- [3] N. H. Sari, I. N. G. Wardana, Y. S. Irawan, and E. Siswanto, (2018) "Characterization of the Chemical, Physical, and Mechanical Properties of NaOH-treated Natural Cellulosic Fibers from Corn Husks" *Journal of Natural Fibers* 15: 545–558. DOI: [10.1080/15440478.2017.1349707](https://doi.org/10.1080/15440478.2017.1349707).
- [4] S. O. Ismail, E. Akpan, and H. N. Dhakal, (2022) "Review on natural plant fibres and their hybrid composites for structural applications: Recent trends and future perspectives" *Composites Part C: Open Access* 9: 100322. DOI: <https://doi.org/10.1016/j.jcomc.2022.100322>.
- [5] Q. Zhang, Y. Ma, Z. Qi, C. Jia, Y. Yao, and D. Zhang, (2022) "Optimisation on uniformity and compressibility of rapeseed straw cellulose fiber mixtures for straw/mineral hybrid natural fiber composite" *Industrial Crops and Products* 189: 115852. DOI: <https://doi.org/10.1016/j.indcrop.2022.115852>.
- [6] N. H. Sari and Y. A. Padang, (2019) "The characterization tensile and thermal properties of hibiscus tiliaceus cellulose fibers" *IOP Conference Series: Materials Science and Engineering* 539: 012031. DOI: [10.1088/1757-899X/539/1/012031](https://doi.org/10.1088/1757-899X/539/1/012031).
- [7] P. Pandit, M. D. Teli, K. Singha, S. Maiti, and S. Maity, (2021) "Extraction and characterization of novel *Sterculia foetida* fruit shell fibre for composite applications" *Cleaner Engineering and Technology* 4: 100194. DOI: <https://doi.org/10.1016/j.clet.2021.100194>.
- [8] N. H. Sari, A. Rahman, and E. Syafri. *Characterization of Musaceae and Saccharum Officinarum Cellulose Fibers for Composite Application*. 2019.

- [9] N. M. Nurazzi, A. Khalina, M. Chandrasekar, H. A. Aisyah, S. A. Rafiqah, R. A. Ilyas, and Z. M. Hanafee, (2020) "Effect of fiber orientation and fiber loading on the mechanical and thermal properties of sugar palm yarn fiber reinforced unsaturated polyester resin composites" **Polimery** 65: 115–124. DOI: [10.14314/polimery.2020.2.5](https://doi.org/10.14314/polimery.2020.2.5).
- [10] X. Han, L. Ding, Z. Tian, W. Wu, and S. Jiang, (2021) "Extraction and characterization of novel ultrastrong and tough natural cellulosic fiber bundles from manau rattan (*Calamus manan*)" **Industrial Crops and Products** 173: 114103. DOI: <https://doi.org/10.1016/j.indcrop.2021.114103>.
- [11] D. Wahjuningrum, M. Hasanah, R. Departemen, B. Perairan, F. Perikanan, I. Kelautan, and I. P. Bogor, (2016) "Efikasi daun sembukan *Paederia foetida* untuk pencegahan infeksi bakteri *Aeromonas hydrophila* pada ikan nila Efficacy of skunkvine leaves *Paederia foetida* for prevention of *Aeromonas hydrophila* infection on tilapia" **Jurnal Akuakultur Indonesia** 15: 108–116. DOI: [10.19027/jai.15.2.108-116](https://doi.org/10.19027/jai.15.2.108-116).
- [12] N. H. Sari, J. Fajrin, Suteja, and A. Fudholi, (2020) "Characterisation of swellability and compressive and impact strength properties of corn husk fibre composites" **Composites Communications** 18: 49–54. DOI: <https://doi.org/10.1016/j.coco.2020.01.009>.
- [13] B. A. Praveena, A. Buradi, N. Santhosh, V. K. Vasu, J. Hatgundi, and D. Huliya, (2022) "Study on characterization of mechanical, thermal properties, machinability and biodegradability of natural fiber reinforced polymer composites and its Applications, recent developments and future potentials: A comprehensive review" **Materials Today: Proceedings** 52: 1255–1259. DOI: <https://doi.org/10.1016/j.matpr.2021.11.049>.
- [14] A. E. Bekele, H. G. Lemu, and M. G. Jiru, (2022) "Experimental study of physical, chemical and mechanical properties of enset and sisal fibers" **Polymer Testing** 106: 107453. DOI: <https://doi.org/10.1016/j.polymertesting.2021.107453>.
- [15] N. Shanmugasundaram, I. Rajendran, and T. Ramkumar, (2018) "Static, dynamic mechanical and thermal properties of untreated and alkali treated mulberry fiber reinforced polyester composites" **Polymer Composites** 39: E1908–E1919. DOI: <https://doi.org/10.1002/pc.24890>.
- [16] M. Khan, S. Rahamathbaba, M. A. Mateen, D. V. R. Shankar, and M. M. Hussain, (2019) "Effect of NaOH treatment on mechanical strength of banana/epoxy laminates" **Polymers from Renewable Resources** 10: 19–26. DOI: [10.1177/2041247919863626](https://doi.org/10.1177/2041247919863626).
- [17] N. A. F. M. Nasir, J. Jamaluddin, Z. Zainudin, M. M. Busheri, N. Adrus, F. S. S. Azim, and R. Hasham, (2020) "The effect of alkaline treatment onto physical, thermal, mechanical and chemical properties of Lemba leaves fibres as new resources of biomass" **Pertanika Journal of Science and Technology** 28: 1531–1547. DOI: [10.47836/pjst.28.4.21](https://doi.org/10.47836/pjst.28.4.21).
- [18] S. Maity, P. Paul, K. Singha, D. P. Gon, and M. Singha, (2012) "A Review on Jute Nonwovens: Manufacturing, Properties and Applications Engineering Fibers for Fog Harvesting and Interfacial Solar Water Purification View project Electro-conductive textiles View project A Review on Jute Nonwovens: Manufacturing, Properties and Applications" **International Journal of Textile Science** 2012: 36–43. DOI: [10.5923/j.textile.20120105.02](https://doi.org/10.5923/j.textile.20120105.02).
- [19] R. Liu, H. Xiao, S. D. Pang, J. Geng, and H. Yang, (2020) "Application of *Sterculia foetida* petiole wastes in lightweight pervious concrete" **Journal of Cleaner Production** 246: 118972. DOI: <https://doi.org/10.1016/j.jclepro.2019.118972>.
- [20] A. Amiri, Z. Triplett, A. Moreira, N. Brezinka, M. Alcock, and C. A. Ulven, (2017) "Standard density measurement method development for flax fiber" **Industrial Crops and Products** 96: 196–202. DOI: <https://doi.org/10.1016/j.indcrop.2016.11.060>.
- [21] A. Bazargan, T. Gebreegziabher, C.-W. Hui, and G. McKay, (2014) "The effect of alkali treatment on rice husk moisture content and drying kinetics" **Biomass and Bioenergy** 70: 468–475. DOI: <https://doi.org/10.1016/j.biombioe.2014.08.018>.
- [22] O. Faruk, A. K. Bledzki, H.-P. Fink, and M. Sain, (2012) "Biocomposites reinforced with natural fibers: 2000–2010" **Progress in Polymer Science** 37: 1552–1596. DOI: <https://doi.org/10.1016/j.progpolymsci.2012.04.003>.
- [23] B. S. L. Brito, F. V. Pereira, J.-L. Putaux, and B. Jean, (2012) "Preparation, morphology and structure of cellulose nanocrystals from bamboo fibers" **Cellulose** 19: 1527–1536. DOI: [10.1007/s10570-012-9738-9](https://doi.org/10.1007/s10570-012-9738-9).
- [24] S. G. Subramanian, R. Rajkumar, and T. Ramkumar, (2021) "Characterization of Natural Cellulosic Fiber from *Cereus Hildmannianus*" **Journal of Natural Fibers** 18: 343–354. DOI: [10.1080/15440478.2019.1623744](https://doi.org/10.1080/15440478.2019.1623744).

- [25] K. H. Reddy, R. M. Reddy, M. Ramesh, D. M. Krishnudu, B. M. Reddy, and H. R. Rao, (2021) "Impact of Alkali Treatment on Characterization of Tapsi (*Sterculia Urens*) Natural Bark Fiber Reinforced Polymer Composites" **Journal of Natural Fibers** 18: 378–389. DOI: [10.1080/15440478.2019.1623747](https://doi.org/10.1080/15440478.2019.1623747).
- [26] G. M. A. Khan, M. S. A. Shams, M. R. Kabir, M. A. Gafur, M. Terano, and M. S. Alam, (2013) "Influence of chemical treatment on the properties of banana stem fiber and banana stem fiber/coir hybrid fiber reinforced maleic anhydride grafted polypropylene/low-density polyethylene composites" **Journal of Applied Polymer Science** 128: 1020–1029. DOI: <https://doi.org/10.1002/app.38197>.
- [27] B. M. Cherian, A. L. Leão, S. F. de Souza, S. Thomas, L. A. Pothan, and M. Kottaisamy, (2010) "Isolation of nanocellulose from pineapple leaf fibres by steam explosion" **Carbohydrate Polymers** 81: 720–725. DOI: <https://doi.org/10.1016/j.carbpol.2010.03.046>.
- [28] R. A. Ilyas, S. M. Sapuan, M. R. Ishak, and E. S. Zainudin, (2017) "Effect of delignification on the physical, thermal, chemical, and structural properties of sugar palm fibre" **BioResources** 12: 8734–8754. DOI: [10.15376/biores.12.4.8734-8754](https://doi.org/10.15376/biores.12.4.8734-8754).
- [29] M. Truong, W. Zhong, S. Boyko, and M. Alcock, (2009) "A comparative study on natural fibre density measurement" **The Journal of The Textile Institute** 100: 525–529. DOI: [10.1080/00405000801997595](https://doi.org/10.1080/00405000801997595).
- [30] M. V. Maheshwaran, N. R. J. Hyness, P. Senthama-raikannan, S. S. Saravanakumar, and M. R. Sanjay, (2018) "Characterization of natural cellulosic fiber from *Epipremnum aureum* stem" **Journal of Natural Fibers** 15: 789–798. DOI: [10.1080/15440478.2017.1364205](https://doi.org/10.1080/15440478.2017.1364205).
- [31] M. Arsyad, (2017) "Effect of Alkali Treatment on The Coconut Fiber Surface" **ARPN Journal of Engineering and Applied Sciences** 12:
- [32] Y. Wu, Y. Zheng, F. Yang, and L. Yang, (2021) "Preparation process and characterization of mechanical properties of twisted bamboo spun fiber bundles" **Journal of Materials Research and Technology** 14: 2131–2139. DOI: <https://doi.org/10.1016/j.jmrt.2021.07.080>.
- [33] M. N. Norizan, K. Abdan, M. S. Salit, and R. Mohamed, (2017) "Physical, mechanical and thermal properties of sugar palm yarn fibre loading on reinforced unsaturated polyester composites." **Journal of Physical Science** 28(3):
- [34] D. Atalie and R. K. Gideon, (2018) "Extraction and characterization of Ethiopian palm leaf fibers" **Research Journal of Textile and Apparel** 22: 15–25. DOI: [10.1108/RJTA-06-2017-0035](https://doi.org/10.1108/RJTA-06-2017-0035).
- [35] D. Watkins, M. Nuruddin, M. Hosur, A. Tcherbi-Narteh, and S. Jeelani, (2015) "Extraction and characterization of lignin from different biomass resources" **Journal of Materials Research and Technology** 4: 26–32. DOI: <https://doi.org/10.1016/j.jmrt.2014.10.009>.
- [36] J. Sahari, S. M. Sapuan, E. S. Zainudin, and M. A. Maleque, (2013) "Mechanical and thermal properties of environmentally friendly composites derived from sugar palm tree" **Materials Design** 49: 285–289. DOI: <https://doi.org/10.1016/j.matdes.2013.01.048>.
- [37] A. Oushabi, S. Sair, F. O. Hassani, Y. Abboud, O. Tanane, and A. E. Bouari, (2017) "The effect of alkali treatment on mechanical, morphological and thermal properties of date palm fibers (DPFs): Study of the interface of DPF–Polyurethane composite" **South African Journal of Chemical Engineering** 23: 116–123. DOI: <https://doi.org/10.1016/j.sajce.2017.04.005>.
- [38] R. Vijay, A. Vinod, D. L. Singaravelu, M. R. Sanjay, and S. Siengchin, (2021) "Characterization of chemical treated and untreated natural fibers from *Penisetum orientale* grass- A potential reinforcement for lightweight polymeric applications" **International Journal of Lightweight Materials and Manufacture** 4: 43–49. DOI: <https://doi.org/10.1016/j.ijlmm.2020.06.008>.