

# Paper 21 open access : Effect of Precipitated Calcium Carbonate on Physical, Mechanical and Thermal Properties of Cassava Starch Bioplastic Composites

Full paper dapat dilihat di bagian bawah ini

ISSN: 2088-5334

Vol 1, No 2 (2011)

## International Journal on Advanced Science Engineering Information Technology

Available online at  
<http://ijaseit.insightsociety.org>

Advanced Science Image processing image retrieval microprocessor  
Back Projection fuzzy Engineering lumina Cell analysis Biometric  
Mobile Agent Interpolation Soft Tissue hydrothermal stability Juniper tree  
Sampling Theorem Magnetic field various structure acidity Malaria  
Parsimony Database Server Robot Operation Image extraction Winecell  
Graphical User Interface Virus compensation Life Cycle Cost  
Current shaping Phylogenetic Analysis Sensor Networks Energy Saving  
Metamorphic Virus neural network Predictive Tools Energy Optimization  
parallel part Obfuscation Techniques Architecture Router Image matching  
Power factor Obfuscation Techniques Predictive Tools Regression Analysis  
Boost regulator catalyst Construction Delay Predictive Tools Regression Analysis  
breast phantom Effects of Delay Predictive Tools Regression Analysis  
Information Technology soybean Current harmonics Surveillance

insight  
www.insightsociety.org

## Effect of Precipitated Calcium Carbonate on Physical, Mechanical and Thermal Properties of Cassava Starch Bioplastic Composites

Edi Syafri, Anwar Kasim, Hairul Abral, Alfi Asben

[IJASEIT - Article \(insightsociety.org\)](http://insightsociety.org)

### Editorial Team

#### Editor in Chief :

Rahmat Hidayat, (Scopus ID: 57191265401) Politeknik Negeri Padang, INDONESIA

#### Associate Editors :

Taufik, (Scopus ID: 23670809800), California Polytechnic State University, USA  
Haitham Alali, (Scopus ID: 49963007000), Amman Arab University, JORDAN  
Wan Mohtar Wan Yusoff, (Scopus ID: 15019967700), Univ. Kebangsaan Malaysia, MALAYSIA  
Halimah Badioze Zaman, (Scopus ID: 25825801600), Univ. Kebangsaan Malaysia, MALAYSIA  
Son Radu, (Scopus ID: 7005251005), Universiti Putra Malaysia, Malaysia, MALAYSIA  
Mohd Razi Ismail, (Scopus ID: 25957691400), Universiti Putra Malaysia, MALAYSIA  
Takashi Oku, (Scopus ID: 56275094900), Prefectural University of Hiroshima, JAPAN  
Kohei Nakano, (Scopus ID: 7402011766), Gifu University, JAPAN  
Nurul Huda, (Scopus ID: 6701695514), Universiti Malaysia Sabah, MALAYSIA  
Yandra Arkeman, (Scopus ID: 55946558300), Bogor Agriculture University, INDONESIA  
Sate Sampattagul, (Scopus ID: 7801640861), Chiangmai University, THAILAND  
Peeyush Soni, (Scopus ID: 9248907800), Asian Institute of Technology, THAILAND  
Yolanda Lechon Perez, (Scopus ID: 6602826000), Ciemat, Madrid, SPAIN  
Gabriele Arcidiacono (Scopus ID: 56656284600), G. Marconi University, ITALY  
Alessandra Pieroni (Scopus ID: 25929524500), Marconi International University, Florida - USA  
Alessandro Simonetta (Scopus ID: 55344403700), University of Rome Tor Vergata, ITALY  
Rita Muhamad Awang, (Scopus ID: 55957782400), Universiti Putra Malaysia, MALAYSIA  
Anton S Prabuwo, (Scopus ID: 18134309800), King Abdulaziz Univ, SAUDI ARABIA  
P Mangala C S De Silva, (Scopus ID: 7006461145), University of Ruhuna, SRI LANKA  
Bich Huy Nguyen, (Scopus ID: 36191086100), Nong Lam University, VIETNAM  
Paul Kristiansen, (Scopus ID: 23097563600), University of New England, AUSTRALIA  
Amitava Basu, (Scopus ID: 21833738300), Bidhan Chandra Krishi Vidyalaya, INDIA  
Shahrul Azman Mohd Noah, (Scopus ID: 35087633200), Universiti Kebangsaan Malaysia, MALAYSIA  
Luca Di Nunzio (Scopus ID:57195199010), University of Rome Tor Vergata, ITALY  
Rocco Fazzolari (Scopus ID:36469997900), University of Rome Tor Vergata, ITALY  
Ruben Paul Borg (Scopus ID:55246483600), L-Università ta' Malta, Msida, Malta  
Van Viet Pham (Scopus ID:57200413784), Ho Chi Minh City University of Transport, VIETNAM

#### Editors :

Novizar Nazir, (Scopus ID: 35503777500), Universitas Andalas, INDONESIA  
Rahadian Zainul, (Scopus ID: 56737195700), Universitas Negeri Padang, INDONESIA

# International Journal on Advanced Science, Engineering and Information Technology

## COUNTRY

Indonesia

- Universities and research institutions in Indonesia
- Media Ranking in Indonesia

## SUBJECT AREA AND CATEGORY

- Agricultural and Biological Sciences
  - Agricultural and Biological Sciences (miscellaneous)
- Computer Science
  - Computer Science (miscellaneous)
- Engineering
  - Engineering (miscellaneous)



## PUBLISHER

## H-INDEX

25

Ads by Google

Send feedback Why this ad?

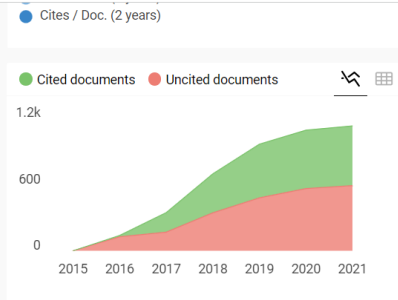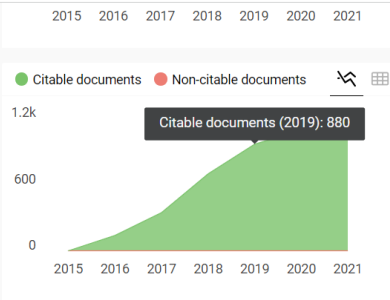

International Journal on Advanced Science...  
 Q3 Agricultural and Biological Sciences (miscellaneous) best quartile  
 SJR 2021 0.25  
 powered by scimagojr.com

Show this widget in your own website  
 Just copy the code below and paste within your html code:  
<https://www.scimagojr.com>

SCImago Graphica  
 Explore, visually communicate and make sense of data with our new data visualization tool.

Ads by Google

Send feedback Why this ad?

Improving the st... Scopus preview - International Jou... (24) WhatsApp - Geoderma - IJASEIT - Open Access Jou... SK Dosen Pengas...

scopus.com/sourceid/21100463068

Gmail Maps YouTube Gmail Edi Syafri - YouTube News

Scopus Preview Author Search Sources Create account Sign in

## Source details

Feedback > Compare sources >

### International Journal on Advanced Science, Engineering and Information Technology

Scopus coverage years: from 2015 to Present  
 Publisher: INSIGHT - Indonesian Society for Knowledge and Human Development  
 ISSN: 2088-5334 E-ISSN: 2460-6952

Subject area: [Agricultural and Biological Sciences: General Agricultural and Biological Sciences](#) [Engineering: General Engineering](#)  
[Computer Science: General Computer Science](#)

Source type: Journal

[View all documents >](#) [Set document alert](#) [Save to source list](#) [Source Homepage](#)

CiteScore 2021  
**1.8**

SJR 2021  
**0.251**

SNIP 2021  
**0.589**

CiteScore CiteScore rank & trend Scopus content coverage

**i** Improved CiteScore methodology

CiteScore 2021 counts the citations received in 2018-2021 to articles, reviews, conference papers, book chapters and data papers published in 2018-2021, and divides this by the number of publications published in 2018-2021. [Learn more >](#)

Type here to search 25°C Hujan ringan 14:32 09/04/2023

Vol. 7 (2017) No. 5

Articles

### **A Study on Facial Expression Recognition Using Local Binary Pattern**

*Shahreen Kasim, Rohayanti Hassan, Nur Hadiana Zaini, Asrafu Syifaa' Ahmad, Azizul Azhar Ramli, Rd Rohmat Saedudin*

pages: 1621-1626 [Full text](#) DOI:10.18517/ijaseit.7.5.3390

### **Grasp Stability Analysis of an Isotropic Direct Driven Three-Finger Soft Robot Hand**

*Elango Natarajan, Mahmud Iwan Solihin, Jeunn Hao Chong*

pages: 1627-1631 [Full text](#) DOI:10.18517/ijaseit.7.5.2526

### **Analysis of Recognition and Educational Needs on Competency of Secondary School Informatics Teachers**

*Youngmin Ko, Yukyeong Lee, Daeyoung Kim, Hanil Kim*

pages: 1632-1637 [Full text](#) DOI:10.18517/ijaseit.7.5.2667

### **Comparative Study of Different Window Sizes Setting in Median Filter for Off-angle Iris Recognition**

*Rohayanti Hassan, Shahreen Kasim, Nurazrin Mohd Esa, Zalmiyah Zakaria*

pages: 1638-1643 [Full text](#) DOI:10.18517/ijaseit.7.5.3393

### **Recognition of Bisindo Alphabets Based on Chain Code Contour and Similarity of Euclidean Distance**

*Dolly Indra, Sarifuddin Madenda, Eri Prasetyo Wibowo*

pages: 1644-1652 [Full text](#) DOI:10.18517/ijaseit.7.5.2746

### **Effect of Precipitated Calcium Carbonate on Physical, Mechanical and Thermal Properties of Cassava Starch Bioplastic Composites**

*Edi Syafri, Anwar Kasim, Hairul Abrol, Alfi Asben*

pages: 1950-1956 [Full text](#) DOI:10.18517/ijaseit.7.5.1292

### **Chemical and Phytochemical Characteristics of Local Corn Silk Powder of Three Different Varieties**

*Haslina Haslina, Danar Praseptiangga, V.Priyo Bintoro, Bambang Pujiasmanto*

pages: 1957-1963 [Full text](#) DOI:10.18517/ijaseit.7.5.2932

### **The Utilization of Fixed Bed Coal Gasification By-Products to Produce Combustible Gas by Auto-thermal Process**

*N Nurhadi, M Ade Andriansyah Efendi, Sapta Rianda*

pages: 1964-1969 [Full text](#) DOI:10.18517/ijaseit.7.5.2104

### **Rainwater Harvesting As a Technological Innovation to Supplying Crop Nutrition through Fertigation**

*Nurpilihan Bafdal, Sophia Dwiratna, Dwi Rustam Kendarto, Edy Suryadi*

pages: 1970-1975 [Full text](#) DOI:10.18517/ijaseit.7.5.3262

### **Population and Diversity of Indigenous Arbuscular Mycorrhizal Fungi from Shallots Rhizosphere in Different Altitudes in West Sumatra**

*Eka Susila, Aswaldi Anwar, Auzar Syarif, Agustian Agustian*

pages: 1886-1893 [Full text](#) DOI:10.18517/ijaseit.7.5.1592

### **Weed Seed Inhibition under Solarization Treatment with Different Mulch Color in Tropical Highland Organic Farming System**

*Nanik Setyowati, Uswatun Nurjanah, Zainal Mukhtar, Fahrurrozi Fahrurrozi, Sigit Sudjatmiko, Mohammad Chozin*

pages: 1894-1899 [Full text](#) DOI:10.18517/ijaseit.7.5.1847

### **The Effect of Tri Poly Phosphate Concentration towards Chitosan-Alginate Micro-particle Characterization and Dissolution Process in Acidic Medium**

*Meri Yulvianti, Jayanudin Jayanudin, Rochmadi Rochmadi, Ajeng Risalina*

pages: 1900-1906 [Full text](#) DOI:10.18517/ijaseit.7.5.2463

### **Shape-Based Single Object Classification Using Ensemble Method Classifiers**

*Nur Shazwani Kamarudin, Mokhairi Makhtar, Syadhah Nor Wan Shamsuddin, Syed Abdullah Fadzli*

pages: 1907-1912 [Full text](#) DOI:10.18517/ijaseit.7.5.1340

### **Wet Season Trials on Growth and Yield of Six Newly Developed Chili Pepper Hybrids at Three Different Locations**

*Catur Herison, Merakati Handajaningsih, Fahrurrozi Fahrurrozi, Rustikawati Rustikawati*

pages: 1913-1919 [Full text](#) DOI:10.18517/ijaseit.7.5.2515

### **Blasting Design Without Subdrilling on Jointed Limestone to Optimize Fragmentation and Blasting Cost**

*Muhammad Taufik Toha, Bochori Bochori, Waluyo Waluyo*

pages: 1920-1926 [Full text](#) DOI:10.18517/ijaseit.7.5.2569

## VOL. 12, NO. 2, APRIL 2019

### Characterization of Musaceae and Saccharum Officinarum Cellulose Fibers for Composite Application

*Nasmi Herlina Sari, Arif Rahman and Edi Syafri*



193-204

### Low-Cost Synthesis Approach for Reversible Authenticator Circuits in QCA Environment

*Bandan Bhoi, Neeraj Kumar Misra, Lafifa Jamal, and Manoranjan Pradhan*



205-220

### Electrical and Microstructural Properties of Silver Thin Films

*Shiva L. U, N. H. Ayachit and Udachan L. A*



221-236

### Analytical Approach Assisted Simulation Study of Si, SiGe, and InP based Bipolar Junction Transistors

*M. R. Jena, S. Mohapatra, A. K. Panda and G. N. Dash*



237-250

### Spectroscopic Study of Titanium Dioxide Thin Films Prepared by Pulsed Laser Deposition

*Rahaf Nasri, Kamal Kayed and Hammoud Al-ourabi*



251-256

### Effect of Deposition Direction on the Properties of Silicon layers Fabricated from Recycled Silicon Powder

*Alaa A. Abdul-Hamead*



123-134

### The Optimum Condition for the Synthesis of Carbon Nanofibers on Activated Carbon to Remove Lead from Aqueous Solution

*Abdullah Al Mamun, Yehya M. Ahmed, Ma'an Fahmi R. Al Khatib, Ahmad T. Jameel, and Mohammed A. Al Saadi*



135-144

### Multi-Response Nanowire Grating-Coupled Surface Plasmon Resonance by Finite Element Method

*Ali Abdulkhaleq Alwahib, Wijdan H. Muttak, and Ali H. Abdulhadi*



145-156

### Characterization and Responsivity of Graphene Loaded Zinc Sulphide within Visible Light Spectrum

*Sabreen A. Khalaf and Iftikhar M. Ali*



157-164

### Robust Design of Kretschmann Plasmonic PCW-based Integrated Biosensor Circuit

*Kalaivani A. Tarumaraja, P. Suthitha Menon, Burhanuddin Yeop Majlis, and Prakash R. Apte*



165-174

### Effect of Iron (111) Oxide (Fe<sub>2</sub>O<sub>3</sub>) as an Additive and Substitution of Quartz with POFA on Physico-Mechanical Properties of Porcelain

*Sani Garba Durumin Iya, Mohamad Zaky Noh, Siti Noraiza Ab Razak, Norazreen Sharip and Nur Azureen Alwi. Kuty*



175-184

## Effect of Precipitated Calcium Carbonate on Physical, Mechanical and Thermal Properties of Cassava Starch Bioplastic Composites

Edi Syafri<sup>\*</sup>, Anwar Kasim<sup>#</sup>, Hairul Abral<sup>\*\*</sup>, Alfi Asben<sup>#</sup>

<sup>\*</sup> Department of Agricultural Technology, Agricultural Polytechnic, Payakumbuh, West Sumatra 26271, Indonesia  
E-mail: edisyafri11@gmail.com

<sup>#</sup> Department of Agriculture Product Technology, Andalas University, West Sumatra 25163, Indonesia  
E-mail: anwar\_ks@yahoo.com, alfi\_asben@yahoo.com

<sup>\*\*</sup> Department of Mechanical Engineering, Andalas University, West Sumatra 25163, Indonesia  
E-mail: hairulabral1966@gmail.com

---

**Abstract**—The development of bioplastic composites from various natural polymers reinforced with Precipitated Calcium Carbonate (PCC) has become a field of increasing interest. In this study, the effect of PCC on the physical, mechanical and thermal properties of a cassava starch matrix composite was examined. The bioplastic composites were made of cassava starch and mixed with glycerol as a plasticizer and 0-10% by weight of PCC. The material was then poured into a mold and oven dried. The physical, thermal and mechanical properties of bioplastic/PCC composites were investigated using Tensile Strength measurements, X-Ray Diffraction, Thermogravimetric Analysis, Scanning Electron Microscopy (SEM), and Fourier Transform Infrared Spectroscopy (FTIR). The optimum tensile strength was obtained upon the addition of 4 % PCC. The addition of PCC improved the thermal stability of bioplastic/PCC composites. The results of X-ray Diffraction testing showed an increase in the crystallinity of the bioplastic/PCC composites with increase in PCC content but there is a decrease in the moisture absorption. SEM images indicated that the PCC filler content was incorporated into the matrix. In general, FTIR indicated the bioplastic/PCC composites were hydrophilic and the addition of PCC reduced the hydrophilic properties by damaging the hydrogen bonding between starch molecules and water.

**Keywords**— cassava starch; precipitated calcium carbonate; tensile strength; thermal stability; moisture absorption

---

### I. INTRODUCTION

Agriculturally produced biopolymers can be used to manufacture bioplastics that can replace synthetic plastics in pharmaceutical and food packaging [1]. Starch is a polysaccharide biopolymer. It is abundant, cheap, and fully biodegradable and forms a matrix that could become a possible replacement of synthetic polymers derived from petroleum without causing environmental pollution. However, starch has some limitations.

Cassava (*Manihot esculenta*) or tapioca is abundantly and cheaply available in Indonesia making it a candidate for bioplastic manufacture. However, it has inferior mechanical and thermal properties. The fragile nature of cassava starch bioplastic can be overcome by adding plasticizers such as glycerol or sorbitol. These increase flexibility but reduce the strength [3]. As a starch, it is also hydrophilic and absorbs water from the atmosphere in storage [2]. Various efforts

have been made to improve the mechanical properties by using natural fibers/biomass as a reinforcement. Natural fibers that have been used as fillers in these biocomposites include pineapple leaf fiber, kenaf fiber, water hyacinth fiber, hemp fiber, oil palm empty fruit bunch fiber, palm leaf fiber and sago fiber [4], [5].

The thermal stability and mechanical properties of biocomposites can also be improved by adding an inorganic filler such as Calcium Carbonate ( $\text{CaCO}_3$ ).  $\text{CaCO}_3$  increases tensile strength, modulus, flexural strength and heat deformation in polypropylene (PP).  $\text{CaCO}_3$  may also increase fracture resistance in PP [6]. Use of nanoparticle- $\text{CaCO}_3$  as a filler in a PP matrix has been shown to improve thermal, rheological, and mechanical properties [7]. Latinwo et al [8] investigated the effects of different particle sizes and compositions of  $\text{CaCO}_3$  on the mechanical properties of polyurethane foam. Baek et al [9] also conducted research on Poly Lactic Acid matrix bioplastics reinforced with PCC and found particle size of PCC was



homogeneously distribution. CaCO<sub>3</sub> particles increased the strength and prevented cracks in PLA/PCC composites. This study investigates the impact of a PCC filler on physical, mechanical and thermal properties of cassava starch bioplastic composites.

## II. MATERIALS AND METHODS

### A. Material

Cassava Starch (Cap Tani, Indonesia), PCC with an average size of 13 μm (Sigma-Aldrich, Germany), and glycerol (PT. Cisadane Raya Chemicals, Tangerang Indonesia) were used for the fabrication of bioplastic/PCC composites.

### B. Fabrication of bioplastics/PCC composites

Fabrication of bioplastic/PCC composites was based on a modification of Tongdeesootorn et al [3]. Cassava starch was dissolved in distilled water (7.14% w/v) and PCC (% w/w from cassava starch) with different concentrations in distilled water (Table 1). Glycerol (25% w/w of cassava starch) was added as a plasticizer. The starch /CaCO<sub>3</sub>/glycerol solution was heated to 100 °C with constant stirring (350 rpm) until gelatinization, cast into 20 x 20 x 0.3 cm<sup>3</sup> rectangular glass molds then oven dried at 50 °C for 17 h. This process is illustrated in Figure 1.

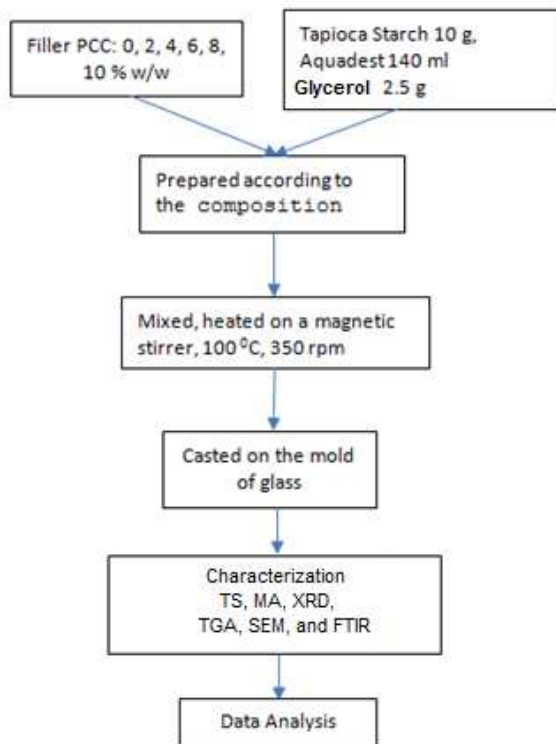


Fig. 1 The process of synthesis of bioplastic/PCC Composites

### C. Mechanical Properties

A 95T Series Com-Ten testing machine was used to measure the tensile strength of the composite samples using a speed of 2 mm/min and room temperature. Tensile testing used standard methods of the American Society for Testing and Materials (ASTM). Tensile strength was tested in accordance with the ASTM D 638 Standard Test Method

for Mechanical Properties of Plastics with specimen dimension type I with sizes as shown in Table 2

TABLE I:  
THE COMPOSITION OF PCC IN FABRICATION BIOPLASTIC/PCC COMPOSITES

Bioplastics/PCC	Composition (g/140 ml distilled water)		
	Cassava starch	Glycerol	PCC
Control/Bioplastics	10	2.5	0
+PCC 2%	10	2.5	0.2
+PCC 4%	10	2.5	0.4
+PCC 6%	10	2.5	0.6
+PCC 8%	10	2.5	0.8
+PCC 10%	10	2.5	1

TABLE II:  
DIMENSIONS OF TENSILE TEST SPECIMENS [10]

Dimensions (see drawings)	For thickness 7(0.28) or under, mm (in)		For thickness Over 7 to 14 (0.28 to 0.55), mm (in)
	Type I	Type II	Type III
W-Width of narrow section <sup>EF</sup>	13 (0.50)	6 (0.25)	19 (0.75)
L-Length of narrow section	57 (2.25)	57 (2.25)	57 (2.25)
WO-Width overall, min <sup>G</sup>	19 (0.75)	19 (0.75)	29 (1.13)
LO-Length overall, min <sup>H</sup>	165 (6.50)	183 (7.20)	50 (2.00)
D-Distance between grips	115 (4.50)	135(5.30)	115 (4.50)
RO-Radius of fillet	76(3.00)	76(3.00)	76(3.00)

### D. Moisture absorption bioplastic/PCC Composites

Moisture absorption was measured using a modification of the method used by Abrial et al. [11]. 20 x 20 x 0.3 mm<sup>3</sup> samples were dried until constant weight then weighed. They were then exposed to 99% humidity at 25 ± 2 °C. Moisture absorption after time t (%) was calculated to be ((Wt-Wo)/Wt) x 100 %, where Wt is the weight of bioplastic/PCC composites after water absorption and Wo was the initial weight of the dried sample.

### E. X-ray Diffraction

The structure of the biocomposites/PCC were studied by X-Ray Diffraction (XRD). The XRD diffractogram was recorded using a series PANalytical's X-ray diffractometer. NI filtered CuKα radiation at wave number 1.54060 Å was used with voltages of 40 kV and 30 mA and scan angles 2θ of 2-100 ° every 20 ° / min.

### F. Thermogravimetric

TGA4000 (Perkin Elmer) was used to measure the degradation of bioplastic/PCC composites with heating. The heating rate was 10 °C per min from 50 to 400 °C. Nitrogen flow rate during the trial was 40 ml per min.

### G. SEM observation

The surface morphology of biocomposite / PCC was observed using SEM images according to the method of Abrial et al. (2014) [11] using a 3400 N series Hitachi SEM.

### H. Fourier Transformed Infrared Spectroscopy (FTIR)

FT-IR analysis was performed from wavenumber 400 to 4000  $\text{cm}^{-1}$  to detect the presence of functional groups in the bioplastic / PCC composite for each PCC concentration using a Frontier (Perkin Elmer) FT-IR spectrometer.

### III. RESULT AND DISCUSSION

#### A. Mechanical Properties of Bioplastic/PCC composites

The mechanical properties of bioplastic/PCC composites can be seen in Figure 2.

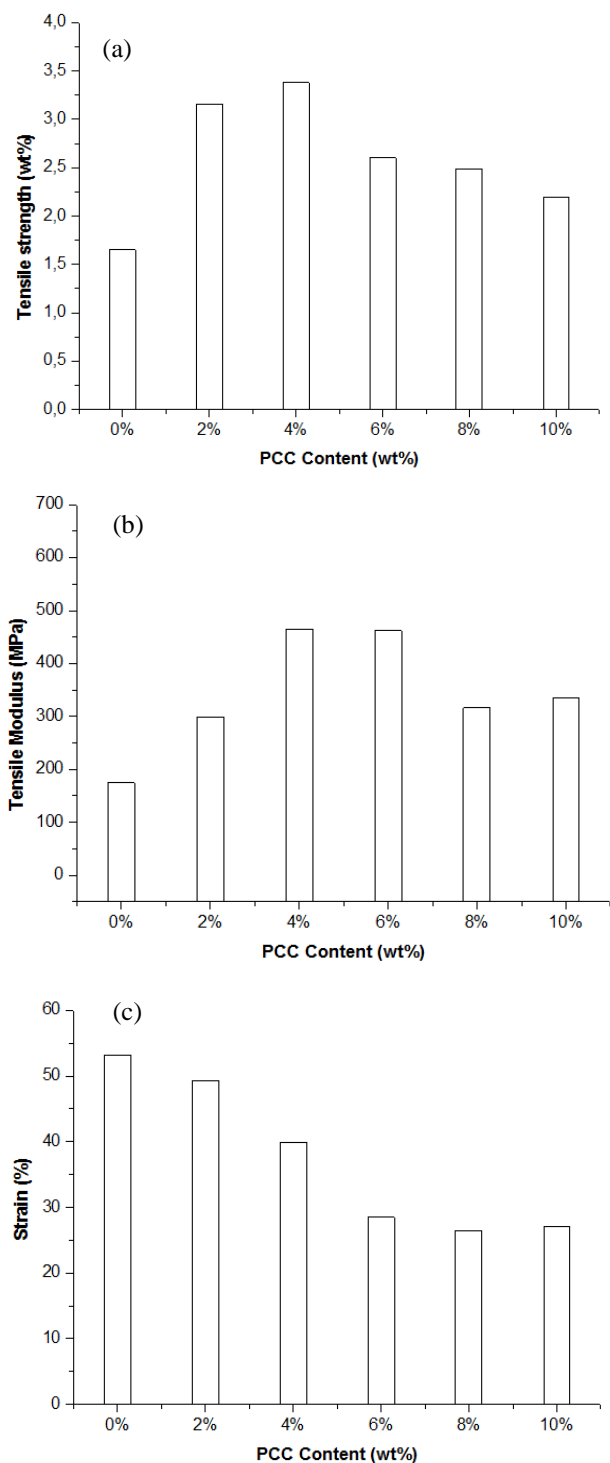


Fig. 2 Effect of PCC on mechanical properties of the composites. (a) tensile strength, (b) tensile modulus and (c) strain

Figure (2 a) shows an increase in tensile strength from 1.65 MPa to 3.38 MPa with the addition of PCC up to 4% (w/w). The modulus of Elasticity (Figure 2 b) increased from 174.61 MPa for pure bioplastic until 645.15 MPa with the addition of 4% PCC.

This increase in tensile strength and modulus of elasticity is related to the hydrogen bonding that occurs between the PCC and the cassava starch matrix. The tensile strength of bioplastic composites is also improved as the small size PCC fills the cavities in the starch matrix during fabrication [12]. Further addition of PCC above 4% reduces tensile strength and modulus of elasticity. This decrease in tensile strength and modulus of elasticity is probably due to the presence of porosities and aggregation which occurs in the matrix as PCC content increases. Wicaksono et al (2013) found that the tensile strength of a cassava starch bioplastic with filler was 1.45 Mpa which increased with the addition 2% and 4 % cellulose nanofibers (CN) to 2.48 MPa and 2.75 MPa, respectively [13]. Saurabh et al (2015) reported that addition of up to 10% nanoclay significantly improved the mechanical properties of nanocomposites however a higher concentration of nano-clay led to a sharp decrease in mechanical properties and caused cracks in the bioplastic composites [14].

The addition of 4% w / w of  $\text{CaCO}_3$  significantly affected the strain of bioplastic/ PCC composites properties, the strain decreased from 53.14% to 39.91% (Fig. 2c). The same is true for all  $\text{CaCO}_3$  additions, the smallest strain of 26.50% occurring for the addition of 8%  $\text{CaCO}_3$ . This result can be attributed to reduced interaction between  $\text{CaCO}_3$  and the tapioca matrix when the excess  $\text{CaCO}_3$  is unable to be absorbed into the matrix. These changes in mechanical characteristics are similar to those caused by other fillers in composites in previous studies [15].

Mechanical properties of the bioplastic composites are highly dependent on the interfacial interaction between matrix and filler. Increased surface contact allows increased hydrogen bonding between matrix and filler strengthening the composite [16]. If the concentration of PCC exceeds 4%, the matrix cannot cover the entire surface of the PCC particles this hydrogen bonding is reduced so strength is reduced also.

#### B. Moisture Absorption Bioplastic/PCC composites

The highest value for moisture absorption of the pure bioplastic (0% PCC) over 21 was 70.59% (Figure 3). The filler effectively reduces the moisture absorption [17]. The hydrophobic nature of the filler reduces absorption of water vapor in the hydrophilic bioplastic as seen over the 42.5 hours. 10% PCC bioplastic had the lowest (53.33%) moisture absorption at 99% relative humidity. Better distribution throughout the bioplastic/PCC composites and the bonding between matrix and filler also affects the absorption of water vapor.

In general, there are two mechanisms for diffusion of water in a composite like this. The gap between the matrix and filler can become a pathway of diffusion water or the cracks and weaknesses at the interface of the fiber and the polymer matrix can produce capillary action. Water absorbed into the polymer can be free water or bound water. Free water can move through the microvoids and pores,

while bound water molecules disperse in the matrix as they are attached to the polar groups of the polymer [18], [19].

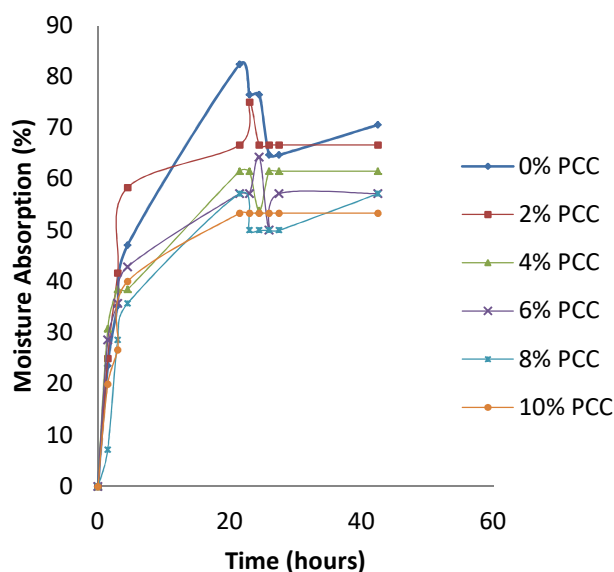


Fig. 3 Moisture absorption of bioplastic/PCC composites

### C. X-Ray Diffraction

Figure 4 shows the XRD profile for biocomposites. Based on information from the Joint Committee on Powder Diffraction Standards database shown in Figure 5, the  $\text{CaCO}_3$  crystal system, is rhombohedral with, a (Å): 4988, b (Å): 4.9880, c (Å): 17 061, and Alpha ( $^\circ$ ): 90, Beta ( $^\circ$ ): 90, Gamma ( $^\circ$ ): 120, while the tapioca matrix cellulose is  $\text{C}_6\text{H}_{10}\text{O}_5$  which has a monoclinic crystal system, a (Å): 7784, b (Å): 8201, c (Å): 10.380, and Alpha ( $^\circ$ ): 90, Beta ( $^\circ$ ): 90, Gamma ( $^\circ$ ): 96.5.

Starch granules can take amorphous and crystalline forms and are mainly composed of amylose and amylopectin. They are destroyed by heat and shear forces from the mixing during the manufacturing process of the biocomposite resulting in a linear amylose polymer. Thermoplastic starch is characterized by broad peaks at  $2\theta = 170$ , indicating a fully amorphous matrix [20].

The diffraction pattern of the  $\text{CaCO}_3$  and tapioca starch films is shown in Fig. 4. The X-ray diffraction pattern of pure tapioca starch films shows low peak intensity. The diffraction peaks are narrower indicating lower crystallinity. The characteristic peaks at  $2\theta$ : 17.10, 20.9. and 22.90 are evident. The diffraction pattern is probably due to the strong interaction between the hydroxyl groups of the starch molecules are replaced by hydrogen bonds formed between plasticizer and starch during processing [21].

The characteristic diffraction peaks of biocomposites /PCC was similar to that of the tapioca starch matrix and pure  $\text{CaCO}_3$ . Characteristic peaks can be detected at an angles  $2\theta$ : 23 $^\circ$ , 36 $^\circ$ , 39 $^\circ$ , 43 $^\circ$  and 480 indicating a good compatibility between tapioca starch containing cellulose with calcium carbonate. The narrowness and high intensity of the peak at  $2\theta$ : 29.5 $^\circ$   $\text{CaCO}_3$  (41.5 $^\circ$ ) shows the high level of calcium carbonate crystallinity.

A widening of the diffraction peaks can be observed in Figure 4, Sun (2014) explains that, according to the

kinematical scattering theory, expansion of the X-ray peak indicates imperfections in the crystal lattice or can be due to the small crystal size [21]. As expected, the addition of PCC nanoparticles can modify the peak intensity of the film biocomposites / PCC indicating higher crystallinity hence explaining the superior strength over pure cassava starch.

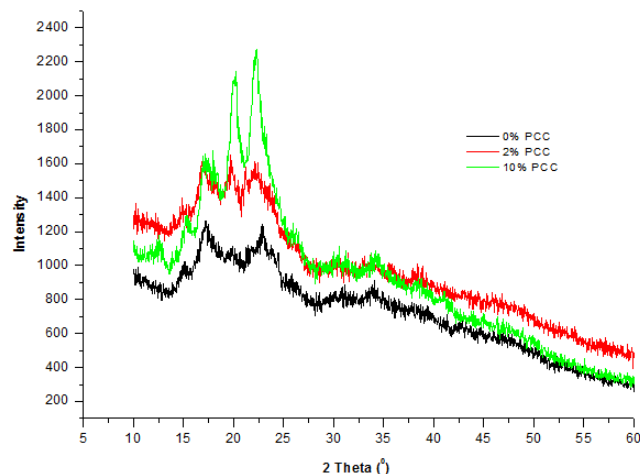


Fig. 4 XRD spectra of bioplastic/PCC composites

### D. Thermogravimetric Analysis

TGA was carried out to study the thermal degradation of Bioplastic/ PCC composites. Figure 5 shows the % weight loss of bioplastic/PCC composites vs temperature for several concentrations of PCC. Composite bioplastics degrade between 250 - 300 $^\circ\text{C}$  and become stable after 340 $^\circ\text{C}$ . The mass loss at temperatures of 50 – 200  $^\circ\text{C}$  was caused by the loss of water. Teixeira et al. (2009) reported that the mass loss of 100  $^\circ\text{C}$  to onset decomposition temperature associated with the evaporation of water [22]. The main mass loss occurs between 250  $^\circ\text{C}$  and 330  $^\circ\text{C}$ , ascribed to the decomposition of the polymeric films [23].

Pure starch bioplastics have a decomposition phase at about 312 $^\circ\text{C}$  corresponding to the temperature of the thermal depolymerization of the starch [24]. Bioplastic/PCC composites with a concentration of 10% PCC have the highest thermal stability. The addition of PCC improves thermal stability indicated by the slower weight loss on heating at this decomposition stage.

### E. SEM observation

SEM analysis was conducted to determine the composite micro-structure (Figure 6). The pure starch bioplastic surface appears homogeneous and smooth (Fig. 6 a and 6 b). As PCC content increases above 4%, the surface becomes visibly uneven with signs of PCC particle aggregation. This confirms the supposition that the decline in mechanical strength of the biocomposite with a concentration of more than 4 % PCC is related to the extra PPC being unable to be absorbed into the matrix and bonded to the starch polymers. Besides, in Figure 6(c) and 6(d) porosity was found to reduce the tensile strength of bioplastic/PCC composites.

### F. Fourier Transformed Infrared Spectroscopy (FTIR)

All FTIR showed a peak was evident at wave number 3200-3600  $\text{cm}^{-1}$  (Figure 7). A peak around 3296  $\text{cm}^{-1}$  indicates a hydrogen bonded O - H stretching [25]. All samples peaks corresponding to a O - H functional groups,

but with slightly different wave numbers between 3296  $\text{cm}^{-1}$  and 3295  $\text{cm}^{-1}$  depending on the PCC levels. The transmittance intensity of this peak decreases with increased levels of PCC filler above 4%, indicating hydrogen bonds between the starch molecules have been damaged [26].

All bioplastic composite samples had a peak in the range 2800-2950  $\text{cm}^{-1}$  corresponding to a C - H functional group [27]. Another peak in the range 1620 - 1650  $\text{cm}^{-1}$  corresponds to water absorption. A peak at 1320-1380  $\text{cm}^{-1}$  in corresponding to bending vibration of a C - H group and C - O of an aromatic ring was also evident [28,29]. Peaks corresponding to bending vibration of C - O, and O - H in the range of 1010-1070  $\text{cm}^{-1}$  was also present in all samples.

Increased levels of PCC filler in bioplastic composites resulted in lower transmittance indicating higher absorption at these wavenumbers. [30]. These results indicate that there have been changes in the starch matrix with the addition of filler chemicals. The interaction between these particles creates hydrogen bonds during processing. These hydrogen bonds strengthen the mechanical properties of the bioplastic composite. Bodirlau et al states that the bonds are probably between hydroxyl and carbonyl groups in the starch and carbonyl and hydroxyl groups and hydroxyl groups in the cellulose [31].


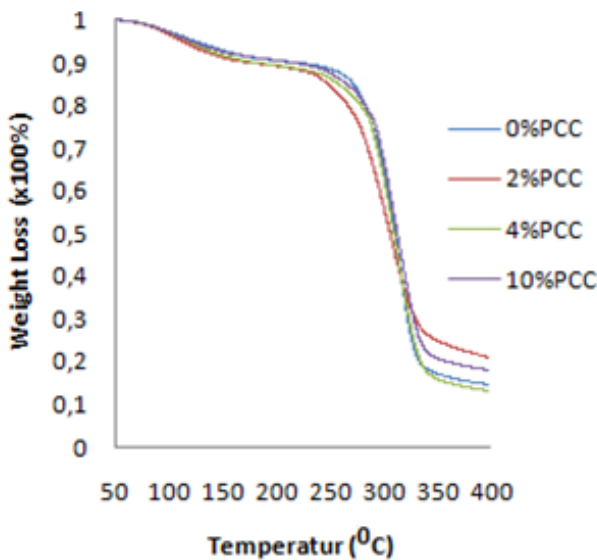


Fig. 5 TGA curves of bioplastic/PCC composites

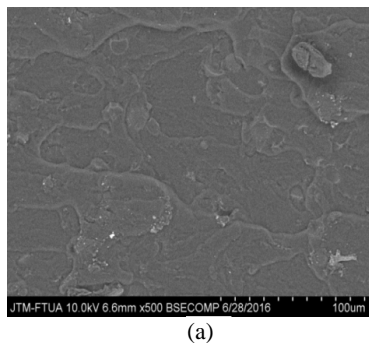

(a)

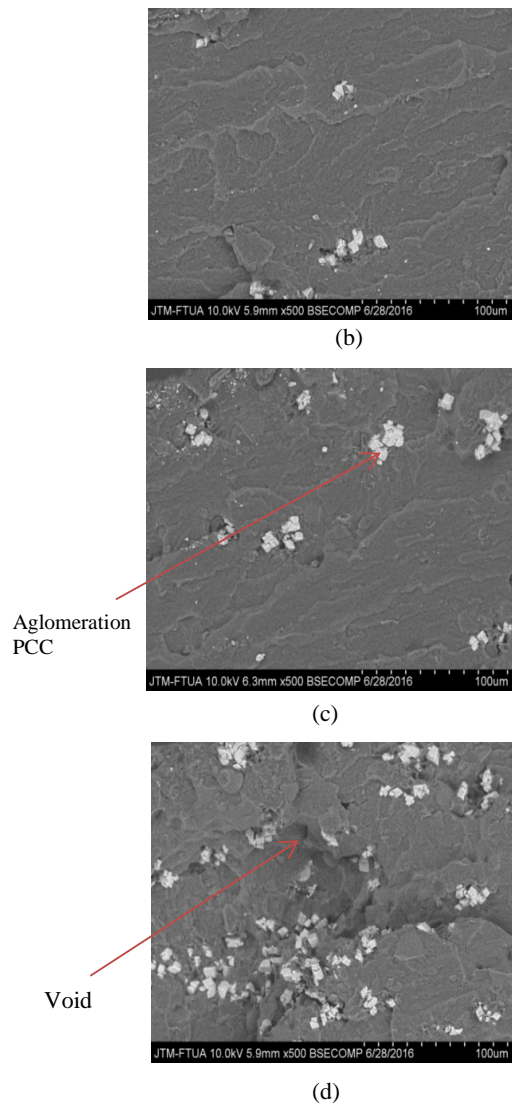


Fig. 6 SEM micrographs of bioplastics/PCC composite (a) 0%PCC, (b) 4%PCC, (c) 8% PCC, and (d) 10% PCC

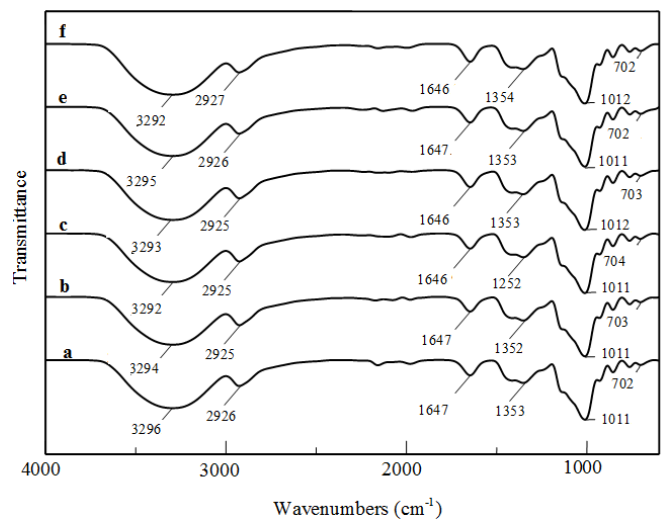


Fig. 7 Infrared spectra of bioplastic/PCCcomposites(a) 0%PCC, (b) 2%PCC, (c) 4% PCC, (d) 6% PCC, (e) 8% PCC and (f) 10% PCC

#### IV. CONCLUSIONS

The addition of precipitated calcium carbonate (PCC) into a cassava starch matrix increased the tensile strength of the resulting bioplastic/PCC composite with an optimum value with the addition of 4 % (w/w) of PCC. This resulted in a composite with tensile strength and modulus of elasticity of 3.38 MPa and 465.15 MPa, respectively. Analysis of TGA graph shows that the addition of PCC improved the thermal stability of the composite. The moisture absorption test indicated that the composites were hydrophilic, although the water absorption properties were reduced from 70.59 % to 53.33 % at 99 % RH after the addition of 10 % PCC. The XRD results test showed bonding between the tapioca starch cellulose and PCC. After PCC content exceeded 4% distribution was no longer even and aggregation occurred decreasing the tensile strength

#### ACKNOWLEDGMENT

The authors thank the Ministry of Research of the Republic of Indonesia, for Scholarship BPPDN 2014, to support the funding of this research.

#### REFERENCES

- [1] Tapia-Blácido, D., Adriana Noemí Mauri, F. C. Menegalli, P. J. A. Sobral, and María Cristina Añón. "Contribution of the starch, protein, and lipid fractions to the physical, thermal, and structural properties of amaranth (*Amaranthus caudatus*) flour films." *Journal of Food Science* 72, no. 5 (2007).
- [2] Lee, Siew Yoong, Han Chen, and Milford A. Hanna. "Preparation and characterization of tapioca starch–poly (lactic acid) nanocomposite foams by melt intercalation based on clay type." *Industrial crops and products* 28, no. 1 (2008): 95-106.
- [3] Tongdeesontorn, Wirongrong, Lisa J. Mauer, Sasitorn Wongruong, Pensiri Sriburi, and Pornchai Rachtanapun. "Mechanical and physical properties of cassava starch-gelatin composite films." *International Journal of Polymeric Materials* 61, no. 10 (2012): 778-792.
- [4] Abrial, H., D. Kadriadi, A. Rodianus, P. Mastariyanto, S. Arief, S. M. Sapuan, and M. R. Ishak. "Mechanical properties of water hyacinth fibers–polyester composites before and after immersion in water." *Materials & Design* 58 (2014): 125-129.
- [5] Rasat, Mohd Sukhairi Mat, Razak Wahab, Zulhisyam Abdul Kari, Ag Ahmad Mohd Yunus, Janshah Moktar, and Siti Fatimah Mhd Ramle. "Strength properties of bio-composite lumbers from lignocelluloses of oil palm fronds agricultural residues." *International Journal on Advanced Science, Engineering and Information Technology* 3, no. 3 (2013): 199-209.
- [6] Han, Liang, Yong Wang, Li Liu, Fang-ming Xiang, Ting Huang, and Zuo-wan Zhou. "Crystallization, mechanical and thermal properties of sorbitol derivatives nucleated polypropylene/calcium carbonate composites." *Chinese Journal of Polymer Science* 28, no. 4 (2010): 457-466.
- [7] Chatterjee, Aniruddha, and Satyendra Mishra. "Rheological, thermal and mechanical properties of nano-calcium carbonate (CaCO<sub>3</sub>)/Poly (methyl methacrylate)(PMMA) core-shell nanoparticles reinforced polypropylene (PP) composites." *Macromolecular Research* 21, no. 5 (2013): 474-483.
- [8] Latinwo, Ganiyu K., David S. Aribike, Layioye O. Oyekunle, Akpoveta A. Susu, and Semiu A. Kareem. "Effects of calcium carbonate of different compositions and particle size distributions on the mechanical properties of flexible polyurethane foam." *Nature and Science* 8, no. 9 (2010): 92-101.
- [9] Baek, Chul Seoung, Kye Hong Cho, and Ji-Whan Ahn. "Effect of Grain Size and Replacement Ratio on the Plastic Properties of Precipitated Calcium Carbonate Using Limestone as Raw Material." *Journal of the Korean Ceramic Society* 51, no. 2 (2014): 127-131.
- [10] American Society for Testing and Materials—ASTM, Testmethod for tensile properties of plastics. ASTM D-638, in:Annual Book of ASTM Standards, ASTM, Philadelphia, vol. 08.01, 2005.
- [11] Abrial, Hairul, Heri Andriyanto, Rendi Samera, S. M. Sapuan, and M. R. Ishak. "Mechanical properties of screw pine (*pandanus odoratissimus*) fibers—unsaturated polyester composites." *Polymer-Plastics Technology and Engineering* 51, no. 5 (2012): 500-506.
- [12] Wicaksono, Rumpoko, Khaswar Syamsu, Indah Yuliasih, Muhamad Nasir, and Karangwangkal Street. "Cellulose nanofibers from cassava bagasse: Characterization and application on tapioca-film." *Cellulose* 3, no. 13 (2013): 79-87.
- [13] Bilbao-Sainz, Cristina, Julien Bras, Tina Williams, Tangi Sénechal, and William Orts. "HPMC reinforced with different cellulose nanoparticles." *Carbohydrate Polymers* 86, no. 4 (2011): 1549-1557.
- [14] Saurabh, Chaturbhuj K., Sumit Gupta, Jitendra Bahadur, S. Mazumder, Prasad S. Variyar, and Arun Sharma. "Mechanical and barrier properties of guar gum based nano-composite films." *Carbohydrate polymers* 124 (2015): 77-84.
- [15] Versino, Florencia, and María Alejandra García. "Cassava (*Manihot esculenta*) starch films reinforced with natural fibrous filler." *Industrial Crops and Products* 58 (2014): 305-314.
- [16] Carvalho, Antonio JF. *Starch: major sources, properties and applications as thermoplastic materials*. Elsevier, Amsterdam, 2008.
- [17] Yang, June-Ho, Jongshin Park, Daehyun Kim, and DaeHoon Lee. "Effects of calcium carbonate as the expanding inhibitor on the structural and mechanical properties of expanded starch/polyvinyl alcohol blends." *Journal of applied polymer science* 93, no. 4 (2004): 1762-1768.
- [18] Penjumras, Patpen, Russly Abdul Rahman, Rosnita A. Talib, and Khalina Abdan. "Mechanical properties and water absorption behaviour of durian rind cellulose reinforced Poly (lactic acid) biocomposites." *International Journal on Advanced Science, Engineering and Information Technology* 5, no. 5 (2015): 343-349.
- [19] Dhakal, H. N., Z. Y. Zhang, and M. O. W. Richardson. "Effect of water absorption on the mechanical properties of hemp fibre reinforced unsaturated polyester composites." *Composites Science and Technology* 67, no. 7 (2007): 1674-1683.
- [20] Angellier, H elene, Sonia Molina-Boisseau, Patrice Dole, and Alain Dufresne. "Thermoplastic starch– waxy maize starch nanocrystals nanocomposites." *Biomacromolecules* 7, no. 2 (2006): 531-539.
- [21] Sun, Qingjie, Tingting Xi, Ying Li, and Liu Xiong. "Characterization of corn starch films reinforced with CaCO<sub>3</sub> nanoparticles." *PLoS one* 9, no. 9 (2014): e106727.
- [22] Teixeira, Eliangela de M., Daniel Pasquini, Ant nio AS Curvelo, Elis ngela Corradini, Mohamed N. Belgacem, and Alain Dufresne. "Cassava bagasse cellulose nanofibrils reinforced thermoplastic cassava starch." *Carbohydrate polymers* 78, no. 3 (2009): 422-431.
- [23] Li, Xiaojing, Chao Qiu, Na Ji, Cuixia Sun, Liu Xiong, and Qingjie Sun. "Mechanical, barrier and morphological properties of starch nanocrystals-reinforced pea starch films." *Carbohydrate polymers* 121 (2015): 155-162.
- [24] Ga n n, Piedad, Robin Zuluaga, Adriana Restrepo, Jalel Labidi, and I naki Mondragon. "Plantain fibre bundles isolated from Colombian agro-industrial residues." *Bioresource Technology* 99, no. 3 (2008): 486-491.
- [25] Cao, X., Y. Chen, P. R. Chang, A. D. Muir, and G. Falk. "Starch-based nanocomposites reinforced with flax cellulose nanocrystals." *Express Polym Lett* 2, no. 7 (2008): 502-510.
- [26] G nzler, Helmut, and Hans-Ulrich Gremlich. "IR spectroscopy. An introduction." (2002).
- [27] Le Troedec, Marianne, David Sedan, Claire Peyratout, Jean Pierre Bonnet, Agn s Smith, Ren  Guinebretiere, Vincent Gloaguen, and Pierre Krausz. "Influence of various chemical treatments on the composition and structure of hemp fibres." *Composites Part A: Applied Science and Manufacturing* 39, no. 3 (2008): 514-522.
- [28] Nacos, M. K., P. Katapodis, C. Pappas, D. Daferera, P. A. Tarantilis, Paul Christakopoulos, and M. Polissiou. "Kenaf xylan—A source of biologically active acidic oligosaccharides." *Carbohydrate polymers* 66, no. 1 (2006): 126-134.
- [29] Jamarun, N., Juita, R., & Rahayuningsih, J., Synthesis and Characterizations Precipitated Calcium Carbonate from Shell Crust (*Anadara granosa*), *Research Journal of Pharmaceutical, Biological and Chemical Sciences*, RJPBCS 6(5), (2015), 136-140.

[30] Pratomy, H., & Rohaeti, E. Bioplastics nata de cassava as an ingredient edible film environmentally friendly. *Saintek Research Journal*, (2015). 16 (2).

[31] R. Bodirlau, C.A. Teaca, & I. Spiridon, (2013). Influence of natural fillers on the properties of starch-based biocomposite films. *Compos. B Eng.*, 44, 575

## Effect of Precipitated Calcium Carbonate on Physical, Mechanical and Thermal Properties of Cassava Starch Bioplastic Composites

Edi Syafri<sup>\*</sup>, Anwar Kasim<sup>#</sup>, Hairul Abral<sup>\*\*</sup>, Alfi Asben<sup>#</sup>

<sup>\*</sup> Department of Agricultural Technology, Agricultural Polytechnic, Payakumbuh, West Sumatra 26271, Indonesia  
E-mail: edisyafri11@gmail.com

<sup>#</sup> Department of Agriculture Product Technology, Andalas University, West Sumatra 25163, Indonesia  
E-mail: anwar\_ks@yahoo.com, alfi\_asben@yahoo.com

<sup>\*\*</sup> Department of Mechanical Engineering, Andalas University, West Sumatra 25163, Indonesia  
E-mail: hairulabral1966@gmail.com

---

**Abstract**—The development of bioplastic composites from various natural polymers reinforced with Precipitated Calcium Carbonate (PCC) has become a field of increasing interest. In this study, the effect of PCC on the physical, mechanical and thermal properties of a cassava starch matrix composite was examined. The bioplastic composites were made of cassava starch and mixed with glycerol as a plasticizer and 0-10% by weight of PCC. The material was then poured into a mold and oven dried. The physical, thermal and mechanical properties of bioplastic/PCC composites were investigated using Tensile Strength measurements, X-Ray Diffraction, Thermogravimetric Analysis, Scanning Electron Microscopy (SEM), and Fourier Transform Infrared Spectroscopy (FTIR). The optimum tensile strength was obtained upon the addition of 4 % PCC. The addition of PCC improved the thermal stability of bioplastic/PCC composites. The results of X-ray Diffraction testing showed an increase in the crystallinity of the bioplastic/PCC composites with increase in PCC content but there is a decrease in the moisture absorption. SEM images indicated that the PCC filler content was incorporated into the matrix. In general, FTIR indicated the bioplastic/PCC composites were hydrophilic and the addition of PCC reduced the hydrophilic properties by damaging the hydrogen bonding between starch molecules and water.

**Keywords**— cassava starch; precipitated calcium carbonate; tensile strength; thermal stability; moisture absorption

---

### I. INTRODUCTION

Agriculturally produced biopolymers can be used to manufacture bioplastics that can replace synthetic plastics in pharmaceutical and food packaging [1]. Starch is a polysaccharide biopolymer. It is abundant, cheap, and fully biodegradable and forms a matrix that could become a possible replacement of synthetic polymers derived from petroleum without causing environmental pollution. However, starch has some limitations.

Cassava (*Manihot esculenta*) or tapioca is abundantly and cheaply available in Indonesia making it a candidate for bioplastic manufacture. However, it has inferior mechanical and thermal properties. The fragile nature of cassava starch bioplastic can be overcome by adding plasticizers such as glycerol or sorbitol. These increase flexibility but reduce the strength [3]. As a starch, it is also hydrophilic and absorbs water from the atmosphere in storage [2]. Various efforts

have been made to improve the mechanical properties by using natural fibers/biomass as a reinforcement. Natural fibers that have been used as fillers in these biocomposites include pineapple leaf fiber, kenaf fiber, water hyacinth fiber, hemp fiber, oil palm empty fruit bunch fiber, palm leaf fiber and sago fiber [4], [5].

The thermal stability and mechanical properties of biocomposites can also be improved by adding an inorganic filler such as Calcium Carbonate ( $\text{CaCO}_3$ ).  $\text{CaCO}_3$  increases tensile strength, modulus, flexural strength and heat deformation in polypropylene (PP).  $\text{CaCO}_3$  may also increase fracture resistance in PP [6]. Use of nanoparticle- $\text{CaCO}_3$  as a filler in a PP matrix has been shown to improve thermal, rheological, and mechanical properties [7]. Latinwo et al [8] investigated the effects of different particle sizes and compositions of  $\text{CaCO}_3$  on the mechanical properties of polyurethane foam. Baek et al [9] also conducted research on Poly Lactic Acid matrix bioplastics reinforced with PCC and found particle size of PCC was

homogeneously distribution. CaCO<sub>3</sub> particles increased the strength and prevented cracks in PLA/PCC composites. This study investigates the impact of a PCC filler on physical, mechanical and thermal properties of cassava starch bioplastic composites.

## II. MATERIALS AND METHODS

### A. Material

Cassava Starch (Cap Tani, Indonesia), PCC with an average size of 13 μm (Sigma-Aldrich, Germany), and glycerol (PT. Cisadane Raya Chemicals, Tangerang Indonesia) were used for the fabrication of bioplastic/PCC composites.

### B. Fabrication of bioplastics/PCC composites

Fabrication of bioplastic/PCC composites was based on a modification of Tongdeesoontorn et al [3]. Cassava starch was dissolved in distilled water (7.14% w/v) and PCC (% w/w from cassava starch) with different concentrations in distilled water (Table 1). Glycerol (25% w/w of cassava starch) was added as a plasticizer. The starch /CaCO<sub>3</sub>/glycerol solution was heated to 100 °C with constant stirring (350 rpm) until gelatinization, cast into 20 x 20 x 0.3 cm<sup>3</sup> rectangular glass molds then oven dried at 50 °C for 17 h. This process is illustrated in Figure 1.

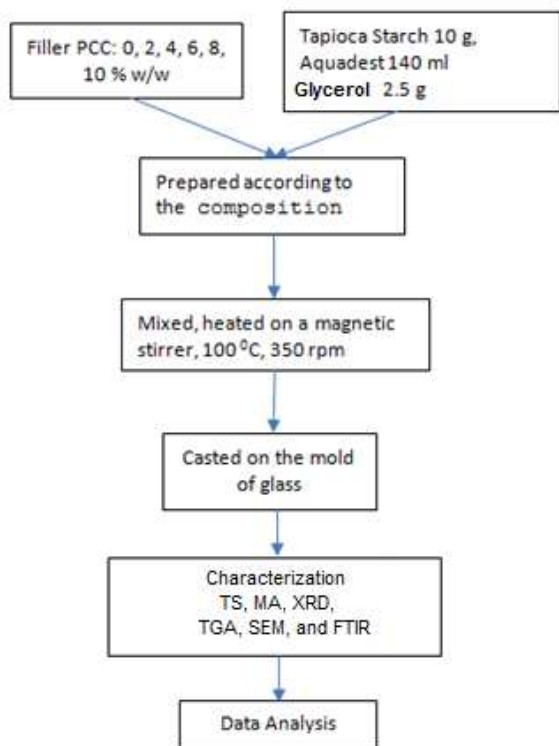


Fig. 1 The process of synthesis of bioplastic/PCC Composites

### C. Mechanical Properties

A 95T Series Com-Ten testing machine was used to measure the tensile strength of the composite samples using a speed of 2 mm/min and room temperature. Tensile testing used standard methods of the American Society for Testing and Materials (ASTM). Tensile strength was tested in accordance with the ASTM D 638 Standard Test Method

for Mechanical Properties of Plastics with specimen dimension type I with sizes as shown in Table 2

TABLE I:  
THE COMPOSITION OF PCC IN FABRICATION BIOPLASTIC/PCC COMPOSITES

Bioplastics/PCC	Composition (g/140 ml distilled water)		
	Cassava starch	Glycerol	PCC
Control/Bioplastics	10	2.5	0
+PCC 2%	10	2.5	0.2
+PCC 4%	10	2.5	0.4
+PCC 6%	10	2.5	0.6
+PCC 8%	10	2.5	0.8
+PCC 10%	10	2.5	1

TABLE II:  
DIMENSIONS OF TENSILE TEST SPECIMENS [10]

Dimensions (see drawings)	For thickness 7(0.28) or under, mm (in)		For thickness Over 7 to 14 (0.28 to 0.55), mm (in)
	Type I	Type II	Type III
W-Width of narrow section <sup>EF</sup>	13 (0.50)	6 (0.25)	19 (0.75)
L-Length of narrow section	57 (2.25)	57 (2.25)	57 (2.25)
WO-Width overall, min <sup>G</sup>	19 (0.75)	19 (0.75)	29 (1.13)
LO-Length overall, min <sup>H</sup>	165 (6.50)	183 (7.20)	50 (2.00)
D-Distance between grips	115 (4.50)	135(5.30)	115 (4.50)
RO-Radius of fillet	76(3.00)	76(3.00)	76(3.00)

### D. Moisture absorption bioplastic/PCC Composites

Moisture absorption was measured using a modification of the method used by Abrial et al. [11]. 20 x 20 x 0.3 mm<sup>3</sup> samples were dried until constant weight then weighed. They were then exposed to 99% humidity at 25 ± 2 °C. Moisture absorption after time t (%) was calculated to be ((Wt-Wo)/Wt) x 100 %, where Wt is the weight of bioplastic/PCC composites after water absorption and Wo was the initial weight of the dried sample.

### E. X-ray Diffraction

The structure of the biocomposites/PCC were studied by X-Ray Diffraction (XRD). The XRD diffractogram was recorded using a series PANalytical's X-ray diffractometer. NI filtered CuKα radiation at wave number 1.54060 Å was used with voltages of 40 kV and 30 mA and scan angles 2θ of 2-100 ° every 20 ° / min.

### F. Thermogravimetric

TGA4000 (Perkin Elmer) was used to measure the degradation of bioplastic/PCC composites with heating. The heating rate was 10 °C per min from 50 to 400 °C. Nitrogen flow rate during the trial was 40 ml per min.

### G. SEM observation

The surface morphology of biocomposite / PCC was observed using SEM images according to the method of Abrial et al. (2014) [11] using a 3400 N series Hitachi SEM.

### H. Fourier Transformed Infrared Spectroscopy (FTIR)



FT-IR analysis was performed from wavenumber 400 to 4000  $\text{cm}^{-1}$  to detect the presence of functional groups in the bioplastic / PCC composite for each PCC concentration using a Frontier (Perkin Elmer) FT-IR spectrometer.

### III. RESULT AND DISCUSSION

#### A. Mechanical Properties of Bioplastic/PCC composites

The mechanical properties of bioplastic/PCC composites can be seen in Figure 2.

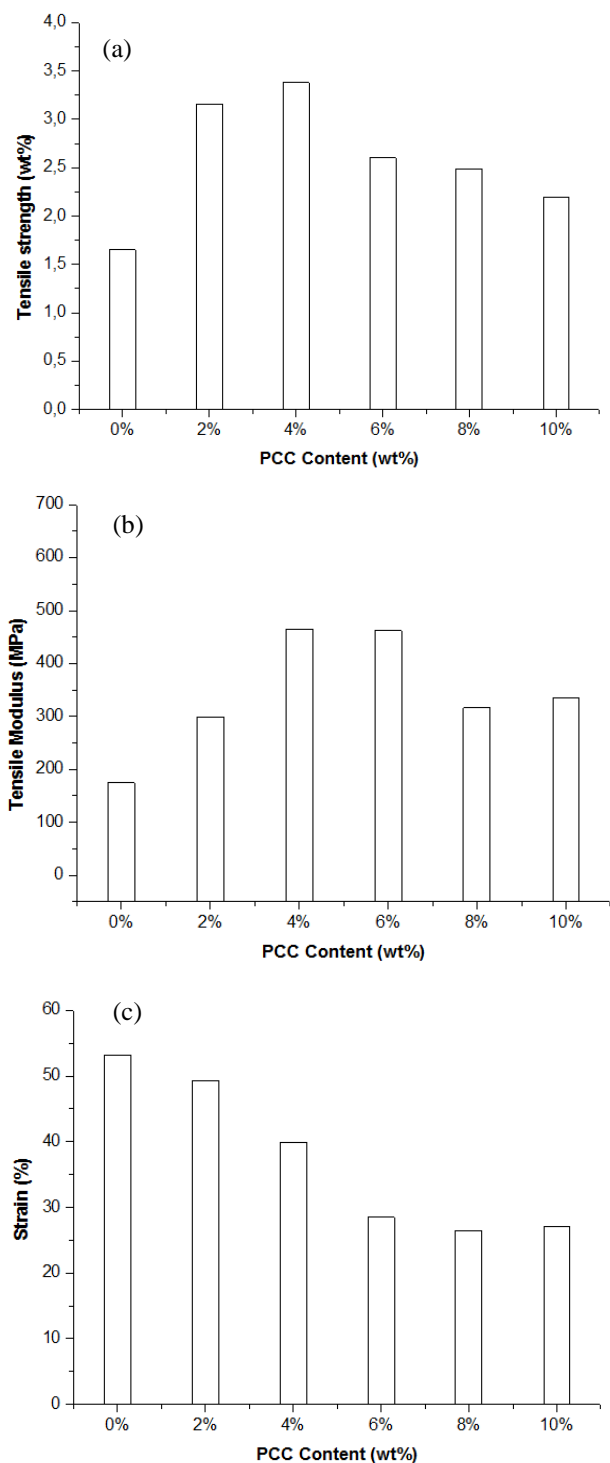


Fig. 2 Effect of PCC on mechanical properties of the composites. (a) tensile strength, (b) tensile modulus and (c) strain

Figure (2 a) shows an increase in tensile strength from 1.65 MPa to 3.38 MPa with the addition of PCC up to 4% (w/w). The modulus of Elasticity (Figure 2 b) increased from 174.61 MPa for pure bioplastic until 645.15 MPa with the addition of 4% PCC.

This increase in tensile strength and modulus of elasticity is related to the hydrogen bonding that occurs between the PCC and the cassava starch matrix. The tensile strength of bioplastic composites is also improved as the small size PCC fills the cavities in the starch matrix during fabrication [12]. Further addition of PCC above 4% reduces tensile strength and modulus of elasticity. This decrease in tensile strength and modulus of elasticity is probably due to the presence of porosities and aggregation which occurs in the matrix as PCC content increases. Wicaksono et al (2013) found that the tensile strength of a cassava starch bioplastic with filler was 1.45 Mpa which increased with the addition 2% and 4 % cellulose nanofibers (CN) to 2.48 MPa and 2.75 MPa, respectively [13]. Saurabh et al (2015) reported that addition of up to 10% nanoclay significantly improved the mechanical properties of nanocomposites however a higher concentration of nano-clay led to a sharp decrease in mechanical properties and caused cracks in the bioplastic composites [14].

The addition of 4% w / w of  $\text{CaCO}_3$  significantly affected the strain of bioplastic/ PCC composites properties, the strain decreased from 53.14% to 39.91% (Fig. 2c). The same is true for all  $\text{CaCO}_3$  additions, the smallest strain of 26.50% occurring for the addition of 8%  $\text{CaCO}_3$ . This result can be attributed to reduced interaction between  $\text{CaCO}_3$  and the tapioca matrix when the excess  $\text{CaCO}_3$  is unable to be absorbed into the matrix. These changes in mechanical characteristics are similar to those caused by other fillers in composites in previous studies [15].

Mechanical properties of the bioplastic composites are highly dependent on the interfacial interaction between matrix and filler. Increased surface contact allows increased hydrogen bonding between matrix and filler strengthening the composite [16]. If the concentration of PCC exceeds 4%, the matrix cannot cover the entire surface of the PCC particles this hydrogen bonding is reduced so strength is reduced also.

#### B. Moisture Absorption Bioplastic/PCC composites

The highest value for moisture absorption of the pure bioplastic (0% PCC) over 21 was 70.59% (Figure 3). The filler effectively reduces the moisture absorption [17]. The hydrophobic nature of the filler reduces absorption of water vapor in the hydrophilic bioplastic as seen over the 42.5 hours. 10% PCC bioplastic had the lowest (53.33%) moisture absorption at 99% relative humidity. Better distribution throughout the bioplastic/PCC composites and the bonding between matrix and filler also affects the absorption of water vapor.

In general, there are two mechanisms for diffusion of water in a composite like this. The gap between the matrix and filler can become a pathway of diffusion water or the cracks and weaknesses at the interface of the fiber and the polymer matrix can produce capillary action. Water absorbed into the polymer can be free water or bound water. Free water can move through the microvoids and pores,

while bound water molecules disperse in the matrix as they are attached to the polar groups of the polymer [18], [19].

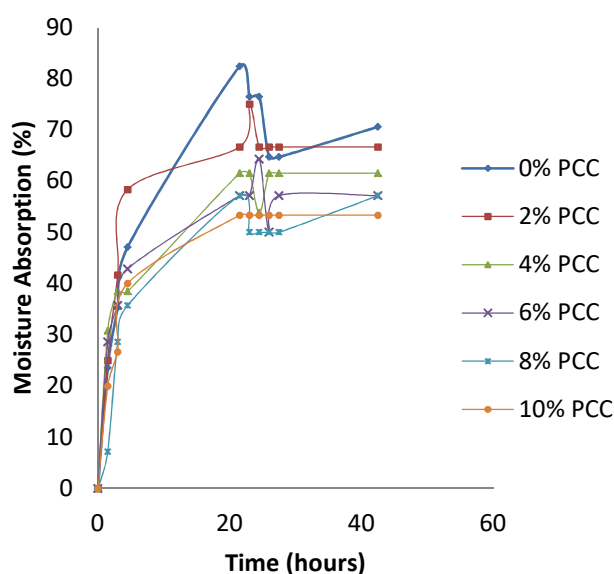


Fig. 3 Moisture absorption of bioplastic/PCC composites

### C. X-Ray Diffraction

Figure 4 shows the XRD profile for biocomposites. Based on information from the Joint Committee on Powder Diffraction Standards database shown in Figure 5, the  $\text{CaCO}_3$  crystal system, is rhombohedral with,  $a$  (Å): 4988,  $b$  (Å): 4.9880,  $c$  (Å): 17 061, and Alpha ( $^\circ$ ): 90, Beta ( $^\circ$ ): 90, Gamma ( $^\circ$ ): 120, while the tapioca matrix cellulose is  $\text{C}_6\text{H}_{10}\text{O}_5$  which has a monoclinic crystal system,  $a$  (Å): 7784,  $b$  (Å): 8201,  $c$  (Å): 10.380, and Alpha ( $^\circ$ ): 90, Beta ( $^\circ$ ): 90, Gamma ( $^\circ$ ): 96.5.

Starch granules can take amorphous and crystalline forms and are mainly composed of amylose and amylopectin. They are destroyed by heat and shear forces from the mixing during the manufacturing process of the biocomposite resulting in a linear amylose polymer. Thermoplastic starch is characterized by broad peaks at  $2\theta = 170$ , indicating a fully amorphous matrix [20].

The diffraction pattern of the  $\text{CaCO}_3$  and tapioca starch films is shown in Fig. 4. The X-ray diffraction pattern of pure tapioca starch films shows low peak intensity. The diffraction peaks are narrower indicating lower crystallinity. The characteristic peaks at  $2\theta$ : 17.10, 20.9. and 22.90 are evident. The diffraction pattern is probably due to the strong interaction between the hydroxyl groups of the starch molecules are replaced by hydrogen bonds formed between plasticizer and starch during processing [21].

The characteristic diffraction peaks of biocomposites /PCC was similar to that of the tapioca starch matrix and pure  $\text{CaCO}_3$ . Characteristic peaks can be detected at an angles  $2\theta$ : 23 $^\circ$ , 36 $^\circ$ , 39 $^\circ$ , 43 $^\circ$  and 480 indicating a good compatibility between tapioca starch containing cellulose with calcium carbonate. The narrowness and high intensity of the peak at  $2\theta$ : 29.5 $^\circ$   $\text{CaCO}_3$  (41.5 $^\circ$ ) shows the high level of calcium carbonate crystallinity.

A widening of the diffraction peaks can be observed in Figure 4, Sun (2014) explains that, according to the

kinematical scattering theory, expansion of the X-ray peak indicates imperfections in the crystal lattice or can be due to the small crystal size [21]. As expected, the addition of PCC nanoparticles can modify the peak intensity of the film biocomposites / PCC indicating higher crystallinity hence explaining the superior strength over pure cassava starch.

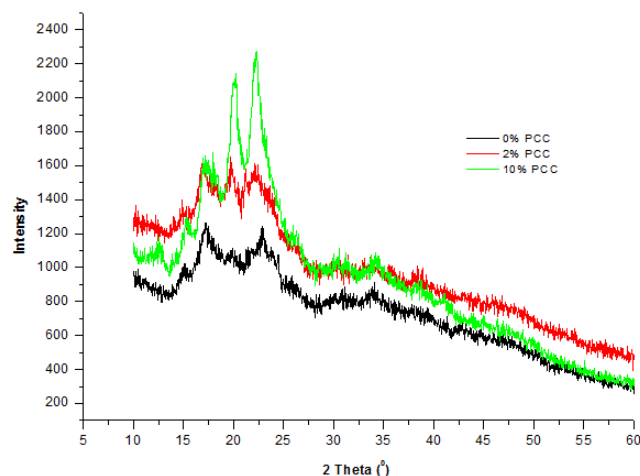


Fig. 4 XRD spectra of bioplastic/PCC composites

### D. Thermogravimetric Analysis

TGA was carried out to study the thermal degradation of Bioplastic/ PCC composites. Figure 5 shows the % weight loss of bioplastic/PCC composites vs temperature for several concentrations of PCC. Composite bioplastics degrade between 250 - 300 $^\circ\text{C}$  and become stable after 340 $^\circ\text{C}$ . The mass loss at temperatures of 50 – 200  $^\circ\text{C}$  was caused by the loss of water. Teixeira et al. (2009) reported that the mass loss of 100  $^\circ\text{C}$  to onset decomposition temperature associated with the evaporation of water [22]. The main mass loss occurs between 250  $^\circ\text{C}$  and 330  $^\circ\text{C}$ , ascribed to the decomposition of the polymeric films [23].

Pure starch bioplastics have a decomposition phase at about 312 $^\circ\text{C}$  corresponding to the temperature of the thermal depolymerization of the starch [24]. Bioplastic/PCC composites with a concentration of 10% PCC have the highest thermal stability. The addition of PCC improves thermal stability indicated by the slower weight loss on heating at this decomposition stage.

### E. SEM observation

SEM analysis was conducted to determine the composite micro-structure (Figure 6). The pure starch bioplastic surface appears homogeneous and smooth (Fig. 6 a and 6 b). As PCC content increases above 4%, the surface becomes visibly uneven with signs of PCC particle aggregation. This confirms the supposition that the decline in mechanical strength of the biocomposite with a concentration of more than 4 % PCC is related to the extra PPC being unable to be absorbed into the matrix and bonded to the starch polymers. Besides, in Figure 6(c) and 6(d) porosity was found to reduce the tensile strength of bioplastic/PCC composites.

### F. Fourier Transformed Infrared Spectroscopy (FTIR)

All FTIR showed a peak was evident at wave number 3200-3600  $\text{cm}^{-1}$  (Figure 7). A peak around 3296  $\text{cm}^{-1}$  indicates a hydrogen bonded O - H stretching [25]. All samples peaks corresponding to a O - H functional groups,

but with slightly different wave numbers between 3296  $\text{cm}^{-1}$  and 3295  $\text{cm}^{-1}$  depending on the PCC levels. The transmittance intensity of this peak decreases with increased levels of PCC filler above 4%, indicating hydrogen bonds between the starch molecules have been damaged [26].

All bioplastic composite samples had a peak in the range 2800-2950  $\text{cm}^{-1}$  corresponding to a C - H functional group [27]. Another peak in the range 1620 - 1650  $\text{cm}^{-1}$  corresponds to water absorption. A peak at 1320-1380  $\text{cm}^{-1}$  in corresponding to bending vibration of a C - H group and C - O of an aromatic ring was also evident [28,29]. Peaks corresponding to bending vibration of C - O, and O - H in the range of 1010-1070  $\text{cm}^{-1}$  was also present in all samples.

Increased levels of PCC filler in bioplastic composites resulted in lower transmittance indicating higher absorption at these wavenumbers. [30]. These results indicate that there have been changes in the starch matrix with the addition of filler chemicals. The interaction between these particles creates hydrogen bonds during processing. These hydrogen bonds strengthen the mechanical properties of the bioplastic composite. Bodirlau et al states that the bonds are probably between hydroxyl and carbonyl groups in the starch and carbonyl and hydroxyl groups and hydroxyl groups in the cellulose [31].


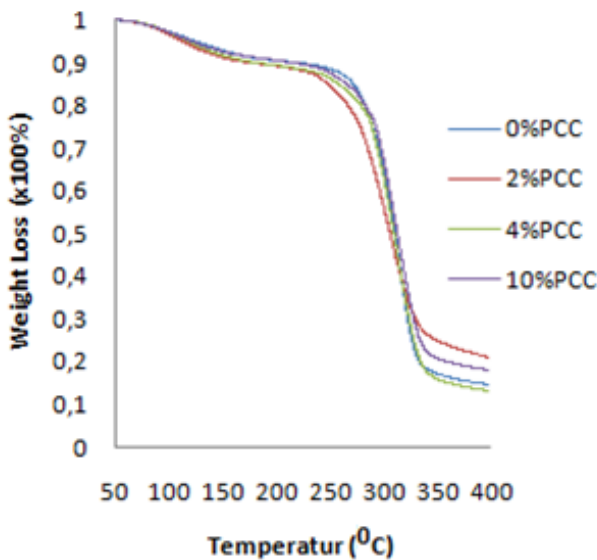


Fig. 5 TGA curves of bioplastic/PCC composites

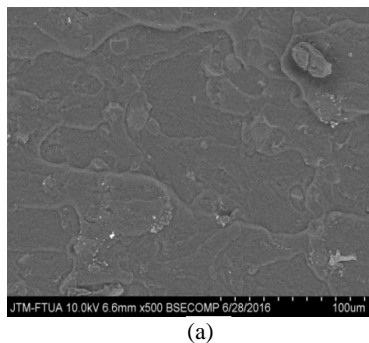

(a)

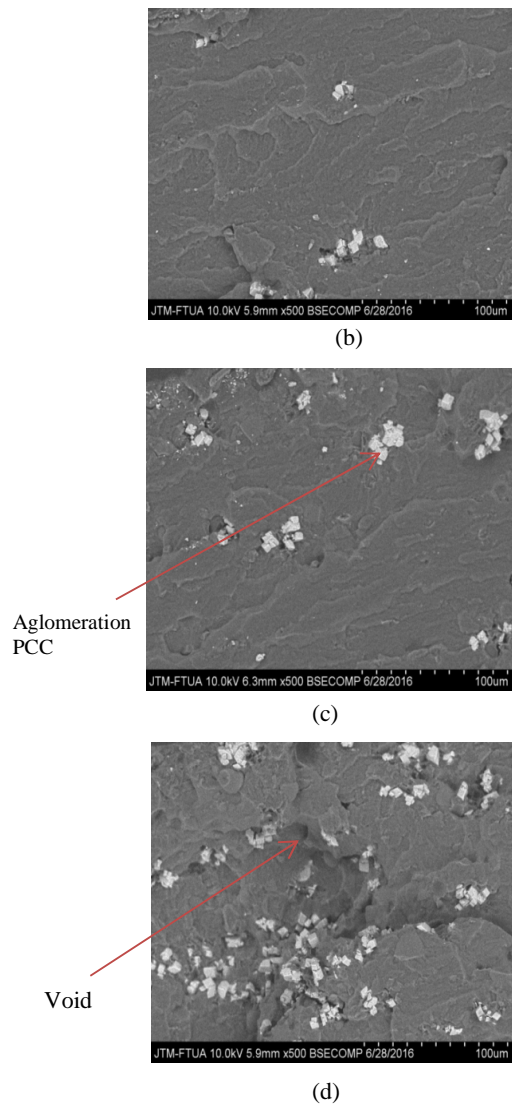


Fig. 6 SEM micrographs of bioplastics/PCC composite (a) 0%PCC, (b) 4%PCC, (c) 8% PCC, and (d) 10% PCC

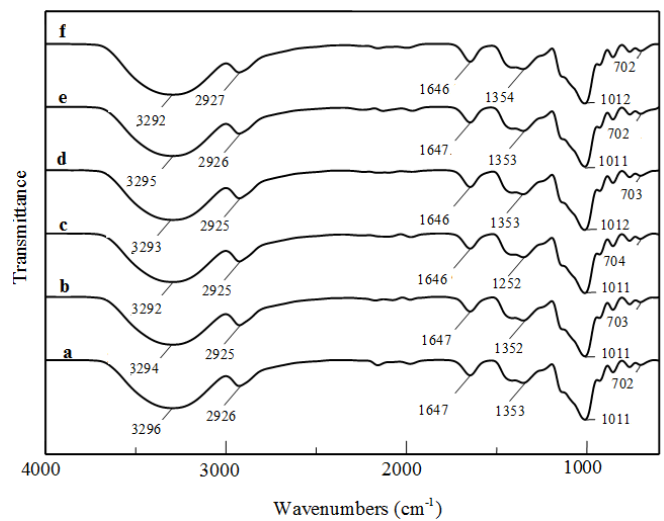


Fig. 7 Infrared spectra of bioplastic/PCCcomposites(a) 0%PCC, (b) 2%PCC, (c) 4% PCC, (d) 6% PCC, (e) 8% PCC and (f) 10% PCC

#### IV. CONCLUSIONS

The addition of precipitated calcium carbonate (PCC) into a cassava starch matrix increased the tensile strength of the resulting bioplastic/PCC composite with an optimum value with the addition of 4 % (w/w) of PCC. This resulted in a composite with tensile strength and modulus of elasticity of 3.38 MPa and 465.15 MPa, respectively. Analysis of TGA graph shows that the addition of PCC improved the thermal stability of the composite. The moisture absorption test indicated that the composites were hydrophilic, although the water absorption properties were reduced from 70.59 % to 53.33 % at 99 % RH after the addition of 10 % PCC. The XRD results test showed bonding between the tapioca starch cellulose and PCC. After PCC content exceeded 4% distribution was no longer even and aggregation occurred decreasing the tensile strength

#### ACKNOWLEDGMENT

The authors thank the Ministry of Research of the Republic of Indonesia, for Scholarship BPPDN 2014, to support the funding of this research.

#### REFERENCES

- [1] Tapia-Blácido, D., Adriana Noemí Mauri, F. C. Menegalli, P. J. A. Sobral, and María Cristina Añón. "Contribution of the starch, protein, and lipid fractions to the physical, thermal, and structural properties of amaranth (*Amaranthus caudatus*) flour films." *Journal of Food Science* 72, no. 5 (2007).
- [2] Lee, Siew Yoong, Han Chen, and Milford A. Hanna. "Preparation and characterization of tapioca starch–poly (lactic acid) nanocomposite foams by melt intercalation based on clay type." *Industrial crops and products* 28, no. 1 (2008): 95-106.
- [3] Tongdeesontorn, Wirongrong, Lisa J. Mauer, Sasitorn Wongruong, Pensiri Sriburi, and Pornchai Rachtanapun. "Mechanical and physical properties of cassava starch-gelatin composite films." *International Journal of Polymeric Materials* 61, no. 10 (2012): 778-792.
- [4] Abrial, H., D. Kadriadi, A. Rodianus, P. Mastariyanto, S. Arief, S. M. Sapuan, and M. R. Ishak. "Mechanical properties of water hyacinth fibers–polyester composites before and after immersion in water." *Materials & Design* 58 (2014): 125-129.
- [5] Rasat, Mohd Sukhairi Mat, Razak Wahab, Zulhisyam Abdul Kari, Ag Ahmad Mohd Yunus, Janshah Mokhtar, and Sitti Fatimah Mhd Ramle. "Strength properties of bio-composite lumbers from lignocelluloses of oil palm fronds agricultural residues." *International Journal on Advanced Science, Engineering and Information Technology* 3, no. 3 (2013): 199-209.
- [6] Han, Liang, Yong Wang, Li Liu, Fang-ming Xiang, Ting Huang, and Zuo-wan Zhou. "Crystallization, mechanical and thermal properties of sorbitol derivatives nucleated polypropylene/calcium carbonate composites." *Chinese Journal of Polymer Science* 28, no. 4 (2010): 457-466.
- [7] Chatterjee, Aniruddha, and Satyendra Mishra. "Rheological, thermal and mechanical properties of nano-calcium carbonate (CaCO<sub>3</sub>)/Poly (methyl methacrylate)(PMMA) core-shell nanoparticles reinforced polypropylene (PP) composites." *Macromolecular Research* 21, no. 5 (2013): 474-483.
- [8] Latinwo, Ganiyu K., David S. Aribike, Layioye O. Oyekunle, Akpoveta A. Susu, and Semiu A. Kareem. "Effects of calcium carbonate of different compositions and particle size distributions on the mechanical properties of flexible polyurethane foam." *Nature and Science* 8, no. 9 (2010): 92-101.
- [9] Baek, Chul Seoung, Kye Hong Cho, and Ji-Whan Ahn. "Effect of Grain Size and Replacement Ratio on the Plastic Properties of Precipitated Calcium Carbonate Using Limestone as Raw Material." *Journal of the Korean Ceramic Society* 51, no. 2 (2014): 127-131.
- [10] American Society for Testing and Materials—ASTM, Testmethod for tensile properties of plastics. ASTM D-638, in:Annual Book of ASTM Standards, ASTM, Philadelphia, vol. 08.01, 2005.
- [11] Abrial, Hairul, Heri Andriyanto, Rendi Samera, S. M. Sapuan, and M. R. Ishak. "Mechanical properties of screw pine (*pandanus odoratissimus*) fibers—unsaturated polyester composites." *Polymer-Plastics Technology and Engineering* 51, no. 5 (2012): 500-506.
- [12] Wicaksono, Rumpoko, Khaswar Syamsu, Indah Yuliasih, Muhamad Nasir, and Karangwangkal Street. "Cellulose nanofibers from cassava bagasse: Characterization and application on tapioca-film." *Cellulose* 3, no. 13 (2013): 79-87.
- [13] Bilbao-Sainz, Cristina, Julien Bras, Tina Williams, Tangi Sénechal, and William Orts. "HPMC reinforced with different cellulose nanoparticles." *Carbohydrate Polymers* 86, no. 4 (2011): 1549-1557.
- [14] Saurabh, Chaturbhuj K., Sumit Gupta, Jitendra Bahadur, S. Mazumder, Prasad S. Variyar, and Arun Sharma. "Mechanical and barrier properties of guar gum based nano-composite films." *Carbohydrate polymers* 124 (2015): 77-84.
- [15] Versino, Florencia, and María Alejandra García. "Cassava (*Manihot esculenta*) starch films reinforced with natural fibrous filler." *Industrial Crops and Products* 58 (2014): 305-314.
- [16] Carvalho, Antonio JF. *Starch: major sources, properties and applications as thermoplastic materials*. Elsevier, Amsterdam, 2008.
- [17] Yang, June-Ho, Jongshin Park, Daehyun Kim, and DaeHoon Lee. "Effects of calcium carbonate as the expanding inhibitor on the structural and mechanical properties of expanded starch/polyvinyl alcohol blends." *Journal of applied polymer science* 93, no. 4 (2004): 1762-1768.
- [18] Penjumras, Patpen, Russly Abdul Rahman, Rosnita A. Talib, and Khalina Abdan. "Mechanical properties and water absorption behaviour of durian rind cellulose reinforced Poly (lactic acid) biocomposites." *International Journal on Advanced Science, Engineering and Information Technology* 5, no. 5 (2015): 343-349.
- [19] Dhakal, H. N., Z. Y. Zhang, and M. O. W. Richardson. "Effect of water absorption on the mechanical properties of hemp fibre reinforced unsaturated polyester composites." *Composites Science and Technology* 67, no. 7 (2007): 1674-1683.
- [20] Angellier, H elene, Sonia Molina-Boisseau, Patrice Dole, and Alain Dufresne. "Thermoplastic starch– waxy maize starch nanocrystals nanocomposites." *Biomacromolecules* 7, no. 2 (2006): 531-539.
- [21] Sun, Qingjie, Tingting Xi, Ying Li, and Liu Xiong. "Characterization of corn starch films reinforced with CaCO<sub>3</sub> nanoparticles." *PloS one* 9, no. 9 (2014): e106727.
- [22] Teixeira, Eliangela de M., Daniel Pasquini, Ant nio AS Curvelo, Elis ngela Corradini, Mohamed N. Belgacem, and Alain Dufresne. "Cassava bagasse cellulose nanofibrils reinforced thermoplastic cassava starch." *Carbohydrate polymers* 78, no. 3 (2009): 422-431.
- [23] Li, Xiaojing, Chao Qiu, Na Ji, Cuixia Sun, Liu Xiong, and Qingjie Sun. "Mechanical, barrier and morphological properties of starch nanocrystals-reinforced pea starch films." *Carbohydrate polymers* 121 (2015): 155-162.
- [24] Ga n n, Piedad, Robin Zuluaga, Adriana Restrepo, Jalel Labidi, and I naki Mondragon. "Plantain fibre bundles isolated from Colombian agro-industrial residues." *Bioresource Technology* 99, no. 3 (2008): 486-491.
- [25] Cao, X., Y. Chen, P. R. Chang, A. D. Muir, and G. Falk. "Starch-based nanocomposites reinforced with flax cellulose nanocrystals." *Express Polym Lett* 2, no. 7 (2008): 502-510.
- [26] G nzler, Helmut, and Hans-Ulrich Gremlich. "IR spectroscopy. An introduction." (2002).
- [27] Le Troedec, Marianne, David Sedan, Claire Peyratout, Jean Pierre Bonnet, Agn s Smith, Ren  Guinebretiere, Vincent Gloaguen, and Pierre Krausz. "Influence of various chemical treatments on the composition and structure of hemp fibres." *Composites Part A: Applied Science and Manufacturing* 39, no. 3 (2008): 514-522.
- [28] Nacos, M. K., P. Katapodis, C. Pappas, D. Daferera, P. A. Tarantilis, Paul Christakopoulos, and M. Polissiou. "Kenaf xylan—A source of biologically active acidic oligosaccharides." *Carbohydrate polymers* 66, no. 1 (2006): 126-134.
- [29] Jamarun, N., Juita, R., & Rahayuningsih, J., Synthesis and Characterizations Precipitated Calcium Carbonate from Shell Crust (*Anadara granosa*), *Research Journal of Pharmaceutical, Biological and Chemical Sciences*, RJPBCS 6(5), (2015), 136-140.

[30] Pratomy, H., & Rohaeti, E. Bioplastics nata de cassava as an ingredient edible film environmentally friendly. *Saintek Research Journal*, (2015). 16 (2).

[31] R. Bodirlau, C.A. Teaca, & I. Spiridon, (2013). Influence of natural fillers on the properties of starch-based biocomposite films. *Compos. B Eng.*, 44, 575